



Trade Science Inc.

Materials Science

An Indian Journal

Full Paper

MSAIJ, 6(1), 2010 [62-67]

Modeling two-dimensional temperature distributions in arc welding of thin plates: Integral method

M.R.Izadpanah*¹, A.R.Ansari Dezfoli², Z.Adabavazeh¹

¹Department of Materials Science and Engineering, Shahid Bahonar University of Kerman,
P. O. Box 76175-133, Kerman, (IRAN)

²Department of Mechanical Engineering, Shahid Bahonar University of Kerman, P. O. Box 76175-133, Kerman, (IRAN)

E-mail: mizadpanah@yahoo.com

Received: 20th January, 2010 ; Accepted: 30th January, 2010

ABSTRACT

In arc welding process, the interesting regions for heat transfer analysis are the fusion zone (FZ) and the heat affected zone (HAZ), where high temperatures are reached. These high temperature levels cause phase transformations and alterations in the mechanical properties of the welded metal. In the present work, a comparison is made between thermal cycles obtained from analytical models base on the integral method with Gaussian (distributed) heat sources and other results base on the concentrated heat source model. Though the integral method is approximate methods, it have proven to give simple solutions with acceptable accuracy for transient heat transfer. The comparison shows that the thermal cycles obtained from the distributed heat source model are more reliable than those obtained from the concentrated heat source model. Also results show that the use of distributed heat source prevents infinite temperatures values near the fusion zone.

© 2010 Trade Science Inc. - INDIA

KEYWORDS

Integral solution;
Welding process;
Gaussian heat source.

INTRODUCTION

Most of the published work on heat transfer during welding processes considers that the heat source is concentrated in a very small volume of the material. After such consideration, analytical solutions are obtained assuming a point, a line or a plane heat source, as those proposed by Rosenthal^[1]. However, measurements of temperatures in the fusion and heat affected zones differ significantly from the values provided by those solutions, since the singularity located at the source origin results in infinite temperature levels. These concentrated source models present higher accuracy in regions where

the temperature does not exceed twenty percent of the material melting point^[2].

In order to avoid the occurrence of unrealistic values at the center and in the vicinity of the fusion zone (FZ), it is more adequate to consider a distributed heat source in the model development. In reality, the heat source is distributed in a finite region of the material, a fact most relevant to the assessment of temperatures near the FZ. There are several models for heat source distribution. The Gaussian distribution firstly suggested by Pavelic et al.^[3], is the most used. Although solutions considering distributed heat sources can be reached both analytically and numerically, there is an increasing ten-

dency to the use of numerical methods.

Izadpanah et al.^[4] developed the mathematical model to analyze the heat transfer characteristics in arc welding Process. They used the similarity solution to model the welding process using thin plates.

The present work, which is an extension of previous work done by authors, presents a new analytical solution base on the integral method to estimate temperature fields in welding, using Gaussian heat sources. A case study, using practical material and parameters, is also simulated to show the main characteristics of the thermal cycles furnished by the developed model. A comparison with the results provided by the concentrated source corresponding solution is carried out.

ANALYTICAL DEVELOPMENT

In the one-dimensional model, the heat flux is considered to occur only in the y direction, as shown in the coordinate system of Figure 1. The following assumptions are made: the heat source moves at a sufficiently high speed (to neglect heat flux in the x direction), and each weld pass fulfills the whole etched groove (no heat flux in the z direction).

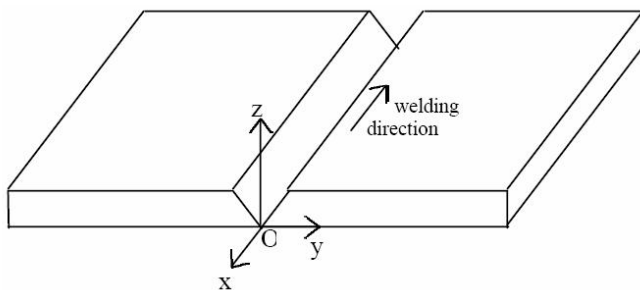


Figure 1 : Coordinate system used in the model.

The formulation of the problem to the first weld pass is made up by the one-dimensional transient heat conduction equation, and its boundary and initial conditions. It is similar to the formulation of the point heat source problem. In terms of θ ($\theta = T - T_0$), it is:

$$\frac{\partial \theta(y, t)}{\partial t} = \alpha \frac{\partial^2 \theta(y, t)}{\partial y^2} \quad (1)$$

$$\theta(y, 0) = 0 \quad (2)$$

$$\theta(\infty, t) = 0 \quad (3)$$

$$Q = \rho c \int_{-\infty}^{\infty} \theta(y, t) dy \quad (4)$$

To take into account the distribution of the heat source,

please refer to Figure 2, where a source with normal or Gaussian distribution is instantaneously applied at $t = 0$ to the surface of a plate. The center C of the source coincides with origin O of the coordinate system xyz. The total power of the source is given by:

$$Q = \int_{-\infty}^{\infty} q_s(y) dy \quad (5)$$

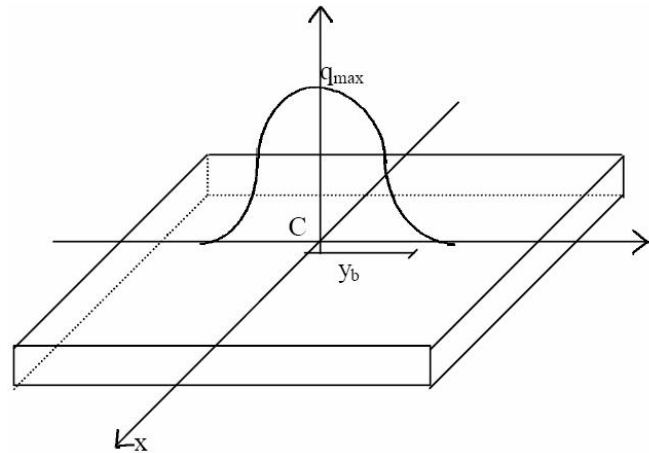


Figure 2 : Gaussian heat source

Solve of the formulation

Initially, it is assumed that the domain is at constant temperature; that is,

$$\theta(y, 0) = 0 \text{ in } 0 < y < \infty \quad (6)$$

For a semi-infinite domain, the necessary second boundary condition for both clamped temperature and heat flux problems is a constant temperature when $y \rightarrow \infty$. Namely,

$$\theta(\infty, t) = 0 \quad (7)$$

We are interested here by the solution for the disturbed temperature field, which is limited by the thermal layer $\delta(t)$ inferior to the length of the domain. Now the condition (3) can be rewritten as,

$$\theta(y, t) = 0 \text{ at } y = \delta(t) \quad (8)$$

By integrating (1) with respect to y over the thermal layer $\delta(t)$, one obtains the Heat Integral equation of the system,

$$\frac{1}{\alpha} \int_0^{\delta(t)} \frac{\partial \theta(y, t)}{\partial t} dy = \int_0^{\delta(t)} \frac{\partial^2 \theta(y, t)}{\partial y^2} dy \quad (9)$$

For right side of equation (9) can write:

$$\int_0^{\delta(t)} \frac{\partial^2 \theta(y, t)}{\partial y^2} dy = \frac{\partial \theta}{\partial y} \Big|_{y=\delta(t)} - \frac{\partial \theta}{\partial y} \Big|_{y=0} = - \frac{\partial \theta}{\partial y} \Big|_{y=0} \quad (10)$$

Full Paper

Note that in our system $\left. \frac{\partial \theta}{\partial y} \right|_{y=\delta(t)}$ is null by the definition of the thermal boundary $\delta(t)$ for left side of equation (9) can write:

$$\int_0^{\delta(t)} \frac{\partial \theta}{\partial t} dy = \frac{d}{dt} \int_0^{\delta(t)} \frac{\partial \theta(y,t)}{\partial y} dy - \theta(\delta(t), t) \frac{d\delta(t)}{dx} = \frac{d}{dt} \int_0^{\delta(t)} \theta(y,t) dy \quad (11)$$

Thus using the equations (10) and (11) the equation (9) is reduced to:

$$-\alpha \left. \frac{\partial \theta}{\partial y} \right|_{y=0} = \frac{d}{dt} \int_0^{\delta(t)} \theta(y,t) dy \quad (12)$$

We have used a temperature profile $\theta = a + by + cy^2$ where the coefficients a , b , and c are functions of $\delta(t)$. To find the coefficients we need one additional boundary condition. For this, already used to construct the Heat Integral equation is straightforward and comes directly from the definition of the thermal layer,

$$\left. \frac{\partial \theta}{\partial y} \right|_{y=\delta(t)} = 0 \quad (13)$$

Using the boundary conditions (2), (4), (8) and (13), we can formulate a solution of as a function of $\delta(t)$.

$$\theta(y,t) = \frac{3}{8} \frac{Q}{\rho c \delta(t)} \left(\left(\frac{y}{\delta(t)} \right)^2 - 2 \left(\frac{y}{\delta(t)} \right) + 1 \right) \quad (14)$$

By substituting equation (14) into the Heat-Integral equation (12), we obtain the thermal layer as a function of time, subjected to the initial condition (6),

$$\delta \frac{d\delta}{dt} = 6\alpha \Rightarrow \delta = \sqrt{12\alpha t} \quad (15)$$

By substituting equation (15) into equation (14) can write:

$$\theta(y,t) = \frac{3}{8} \frac{Q}{\rho c \sqrt{12\alpha t}} \left(\left(\frac{y}{\sqrt{12\alpha t}} \right)^2 - 2 \left(\frac{y}{\sqrt{12\alpha t}} \right) + 1 \right) \quad (16)$$

The gaussian distribution

In the one-dimensional case, the Gaussian distribution of the heat source along the y direction occurs simultaneously at all points of the x direction of welding. The power $q_s(y)$ may be expressed by:

$$q_s(y) = q_{\max} \exp(-By^2) \quad (17)$$

Where:

q_{\max} = q_s maximum value (W/m)

B = coefficient of arc concentration (1/m)

Coefficient B is determined considering a distance y_b in

Equation (17), which corresponds to the distance from the origin to the location where the power is reduced to five percent of its maximum value (Figure 2). Thus,

$$B = \frac{3}{y_b^2} \quad (18)$$

When y_b is large, $q_s(y)$ decreases slowly with y . Substituting Equation (18) in Equation (17) and then in Equation (5), and integrating this equation between $-y_b$ and y_b limits, one obtains:

$$q_{\max} = \frac{\sqrt{3}Q}{\sqrt{\pi} y_b \text{Erf}(\sqrt{3})} \quad (19)$$

Equation (17) may then be written as:

$$q_s(y) = \frac{\sqrt{3}Q}{\sqrt{\pi} y_b \text{Erf}(\sqrt{3})} \exp\left(-\frac{3y^2}{y_b^2}\right) \quad (20)$$

The diffusion process of an instantaneous Gaussian heat source applied to the surface of the material may be obtained by the source method. Let the y coordinate, along which the heat source varies, be divided in small elements dy' . The heat $dQ = q_s(y')dy'$ is supplied to the element dy' at $t = 0$, and may be regarded as an instantaneous point heat source. According to Equation (16), the diffusion process to an instantaneous heat source is:

$$d\theta(y,t) = \frac{3}{8} \frac{dQ}{\rho c \sqrt{12\alpha t}} \left(\left(\frac{y}{\sqrt{12\alpha t}} \right)^2 - 2 \left(\frac{y}{\sqrt{12\alpha t}} \right) + 1 \right) = \frac{3}{8} \frac{q_s(y')(dy')}{\rho c \sqrt{12\alpha t}} \left(\left(\frac{y}{\sqrt{12\alpha t}} \right)^2 - 2 \left(\frac{y}{\sqrt{12\alpha t}} \right) + 1 \right) \quad (21)$$

Substituting Equation (20) in Equation (21), and also By the superposition principle, the temperature change in the y point may be obtained by summing the contributions of all instantaneous concentrated sources dQ , acting along the y coordinate of the material, between $-y_b$ and y_b points:

$$d\theta(y,t) = \frac{3}{8} \int_{-y_b}^{y_b} \frac{\sqrt{3}Q}{\rho c \sqrt{12\pi\alpha t} y_b \text{Erf}(\sqrt{3})} \left(\left(\frac{y}{\sqrt{12\alpha t}} \right)^2 - 2 \left(\frac{y}{\sqrt{12\alpha t}} \right) + 1 \right) \exp\left(-\frac{y'^2}{y_b^2}\right) dy' \quad (22)$$

Solving the integral and rearranging the solution, one obtains:

$$\theta(y,t) = \frac{3}{8} \frac{\sqrt{3\pi} Q \text{Erf}\left(\frac{\sqrt{3}y}{y_b}\right)}{\rho c \pi y_b \sqrt{12\alpha t} \text{Erf}\left(\sqrt{3}\right)} \left(\left(\frac{y}{\sqrt{12\alpha t}} \right)^2 - 2 \left(\frac{y}{\sqrt{12\alpha t}} \right) + 1 \right) \quad (23)$$

The general solution to n passes, in terms of T , is given by:

$$\theta(y,t) = \frac{3}{8} \frac{\sqrt{3\pi} Q \text{Erf}\left(\frac{\sqrt{3}y}{y_b}\right)}{\rho c \pi y_b \text{Erf}\left(\sqrt{3}\right)} \sum_{i=1}^n \frac{1}{12\alpha t - ((i-1)t_p)} \left(\left(\frac{y}{\sqrt{12\alpha(t - (i-1)t_p)}} \right)^2 - 2 \left(\frac{y}{\sqrt{12\alpha(t - (i-1)t_p)}} \right) + 1 \right) \quad (24)$$

MODEL EVALUATION

A comparison between concentrated and distributed heat source models was made through simulation of thermal cycles for three weld passes. Equation (23) was used to calculate the temperatures near the fusion zone, when a Gaussian distributed heat sources is applied. The multipass model with concentrated heat source is given by Eq. (24). In this case, the variable $q_s(y)$ does not have a distribution, and it is calculated by:

$$q_s = Q = \frac{\eta VI}{vz} \quad (25)$$

The waiting time (time between passes) used corresponds to 80 seconds, and the welding process was simulated during a total time of 240 seconds. The ambient temperature is 25°C. The error function in Eq. (24) was evaluated using a polynomial approximation. The properties and parameters used in the simulation are described below.

Material

The evaluation of the proposed model was made considering butt welding of high strength low alloy steel (HSLA) plates, with dimensions 0.13 x 0.10 x 0.25 m (thickness x length bead x width). TABLE 1 shows the physical properties used in the simulation. It is known that the physical properties of the metal change with temperature. However, this variation in the analytical

models results in a non-linear equation, and it is not possible to obtain the solution in closed form. Then, the physical properties are usually taken at a specific temperature, for example, at half the melting point of the material. In this work, they were calculated at 800°C. The values refer to low carbon steels, but they can be used for HSLA steel, as suggested by Hanz et al.^[5]

Welding parameters

In order to fulfill the groove, in butt welding, the usual practice is to increase the heat input from one pass to the next. In the present simulation of a real case, the increase of heat input is obtained by increasing the welding current, the other parameters in Eq. (25) remaining unaltered. However, the current increase causes efficiency to decrease. Then, a different value of efficiency must be used in each pass. The choices of these values were based on the efficiency range for the Gas Metal Arc Welding (GMAW) process, which ranges from 66 to 85%^[6].

The welding parameters used in the simulation are in TABLE 1. The heat input (HI) values were determined by Eq. (25), multiplied by the material thickness. The same HI values were used in the point and Gaussian heat source models. However, in the Gaussian heat source model, only ninety-five percent of HI was applied to the weld. In order to adjust such difference, the HI values in TABLE 2 were multiplied by 1.05 for the Gaussian model.

TABLE 1 : Physical properties of low carbon steel and weld parameters

pass	I(A)	V(V)	v(m/s)	η %	HI(*10 ⁶ j/m)
1	186	26.4	0.005	80	0.79
2	235	26.2	0.005	75	0.92
3	301	25.4	0.005	70	1.07
k (j / ms ⁰ C)			31.67		
pc (J / ms ³⁰ C)			7.14 × 10 ⁶		
a(m / s)			4.44 × 10 ⁻⁶		

In order to verify the capability of the proposed model to reproduce the thermal cycles, some values were chosen for the y and y_b variables. These choices took into account the heat input used in the simulation, and also known values of y_b from the literature, obtained via experimental determination. TABLE 3 shows the y_b values obtained by Kou and Wang^[7], Zacharia et

Full Paper

al.^[8], and Wu^[9], as well as the heat input (HI) used in their analyses. In the present work, the y_b parameter was estimated based on the heat input values showed in TABLE 2. In Eq. (18), the B coefficient was determined for the y_b distance, where the power is reduced to five percent of its maximum value. According to this equation, by increasing the heat input parameter y_b also increases, such that the area under the curve of Figure 2 remains equal to ninety-nine percent of its q_{max} value. Therefore, different values of y_b for each pass were considered, since the heat input increased in the second and third passes. The y_b values used in the simulation were 0.004; 0.0047 and 0.0054 m for the first, second and third pass, respectively.

TABLE 2 : Physical properties of low carbon steel and weld parameters

Author	I(A)	V(V)	v(m/s)	y_b (m)
Kou and Wang ^[6]	100	11	0.0055	0.003
Zacharia et al. ^[7]	175	14	0.0034	0.003
Wu ^[8]	200	20	0.01	0.002

RESULTS AND DISCUSSION

To compare the point and Gaussian heat source models derived from similarity solution^[4] and integral solution, thermal cycles were simulated at two different y locations, namely: y equal to 0.001 m, appropriate for a position near the fusion zone ($y < y_b$), and y equal to 0.003 m, a location at a distance of the same magnitude as the y_b parameter. Figure 3 shows the thermal

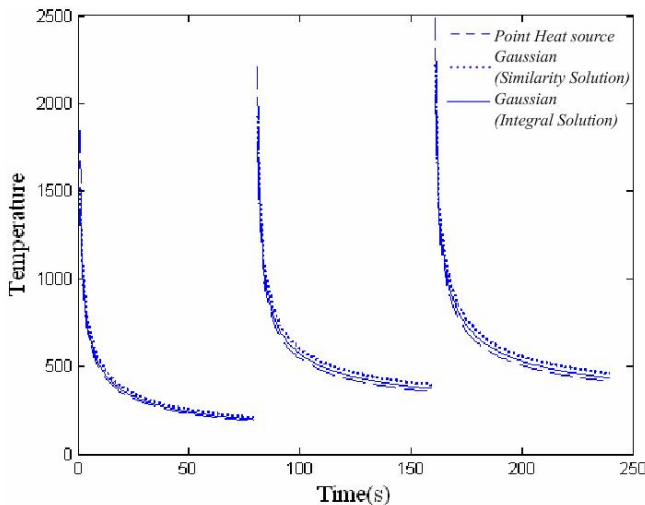


Figure 3 : Thermal cycles for the point and Gaussian heat source models, at $y = 0.001$ m.

cycles obtained after the point and Gaussian heat source models, at $y = 0.001$ m.

It can be observed that the peak temperatures in each pass are higher for the point heat source model than for the Gaussian heat source models. This occurs due to the assumption that the heat input is instantaneously applied over an infinitesimal volume cross-sectioned by the thickness-width plane at the center of the work piece. In the Gaussian heat source model, it is assumed that the heat input is applied over the finite volume, including the y coordinate at the extent of the y_b parameter. Therefore, the peak temperatures produced by the latter model is expectedly more realistic. The previous determination of the peak temperature to be reached at a specific location is interesting, since it indicates fortuitous phase changes. The differences between the temperatures simulated by the three models are described in the TABLE 3. T_1 refers to maximum temperature reached in the first pass; T_2 in the second pass, and so on. It is worth noticing that the correction in the proposed model affect only the peak temperature determination, and no difference is seen in the cooling rate.

TABLE 3 : Peak temperatures reached in each

Tpeak	Point heat source	Gaussian heat source-similarity solution ^[4]	Gaussian heat source-integral solution
T1	1810	1503	1645
T2	2320	1892	2010
T3	2495	2280	2345

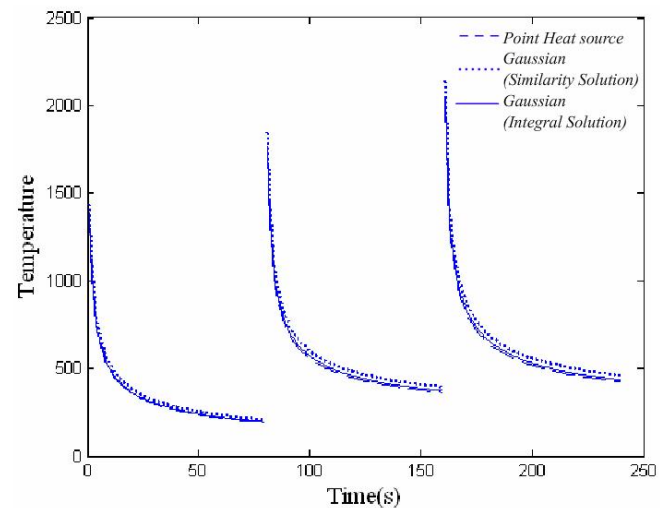


Figure 4 : Thermal cycles for the point and Gaussian heat source models, at $y = 0.003$ m.

In Figure 4, the thermal cycles were simulated using $y = 0.003$ m. It is instrumental to show that, if y is close to y_b , the Gaussian heat source model is equivalent to the point heat source solution. The three models provide results that are practically the same. This means that the point source model at distances far from the fusion zone can correctly predict the temperature fields.

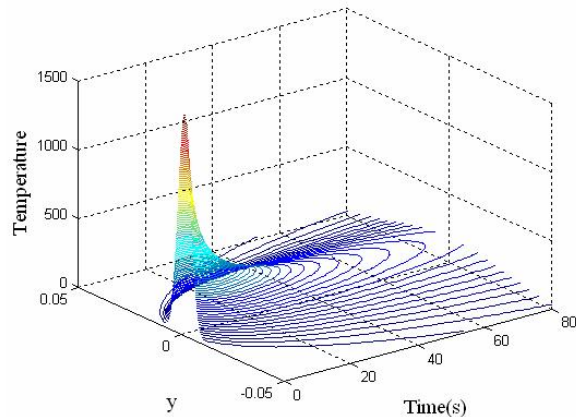
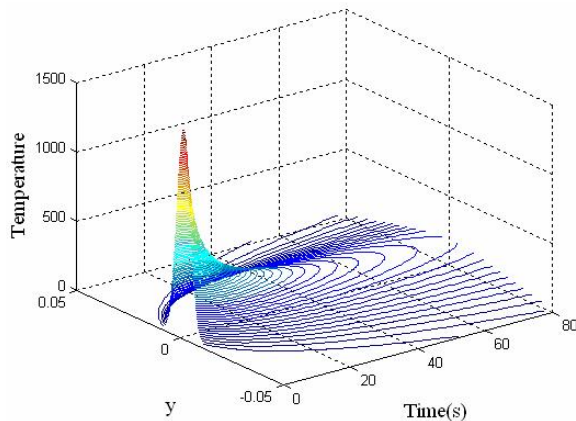
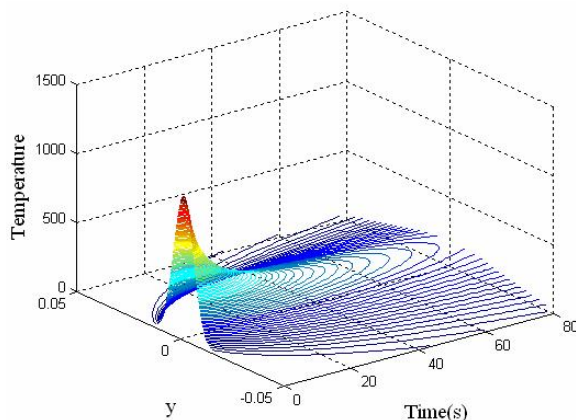
(a) $y = 0.001$ m(b) $y = 0.003$ m(c) $y = 0.009$ m

Figure 5 : 3D Temperature distribution in single cycle arc welding, at $y = 0.001, 0.003$ and 0.009 m.

In Figure 5, the thermal cycles were simulated using $y = 0.001, 0.003$ and 0.009 m

CONCLUSIONS

The main conclusions of this work are:

- the closed form solution obtained allows to estimate the thermal cycles produced by multipass welding process, near the fusion and heat affected zones;
- the distributed heat source in the proposed solution is an important correction for the known model with point source, since this factor allows to obtain temperature values more realistic near to the fusion zone;
- the analytical solution derived from the point source model can be safely used to predict temperature fields away from the fusion zone (FZ) and the heat affected zone (HAZ).

REFERENCES

- [1] D.Rosenthal; *Welding Journal*, **20(5)**, 220s-234s (1941).
- [2] J.Goldak, M.Bibby, A.Chakravarti; *Metallurgical Transactions B*, **15B**, 299-305 (1984).
- [3] V.Pavelic, R.Tanbakuchi, O.A.Uyehara, P.S.Myers; *Welding Journal*, **48(7)**, 295s-305s (1969).
- [4] M.R.Izadpanah, A.R.Ansari Dezfoli, Z.Adabavazeh; *Optimization Mechanical Properties of Austenetic Stainless Steels during Multi-Pass Welding Process*, 3rd Iranian National Conference on Heat Treatment, Iran, 199 (2008).
- [5] Z.Hanz, J.Orozco, J.E.Indacochea, C.H.Chen; *Welding Journal*, **68(9)**, 363s-371s (1989).
- [6] L.E.Svensson; 'Arc Welding Process, in Control of Microstructures and Properties in Steel Arc Welds', CRC Press (1994).
- [7] S.Kou, Y.H.Wang; *Welding Journal*, **65(3)**, 63s-70s (1986).
- [8] T.Zacharia, A.H.Eraslan, D.K.Aidun, S.A.David; *Metallurgical Transactions B*, **20B**, 645-659 (1989).
- [9] C.S.Wu; *Engineering Computations*, **9**, 529-537 (1992).