



Trade Science Inc.

Materials Science

An Indian Journal

Full Paper

MSAIJ, 4(1), 2008 [1-9]

Norfloxacin and sparfloxacin as corrosion inhibitors: comparative study

S.A.Odoemalam¹, N.O.Eddy^{2*}¹Department of Chemistry, Mich. Okpara University of Agriculture, Umudike, (NIGERIA)²Department of Science Technology Akwa Ibom State Polytechnic, Ikot Osurua,
P.M.B.1200, Ikot Ekpene Akwa Ibom State, (NIGERIA)

E-mail: nabukeddy@yahoo.com

Received: 28th August, 2007 ; Accepted: 2nd September, 2007

ABSTRACT

Effect of norfloxacin and sparfloxacin on the corrosion of zinc in 0.001-0.005M H₂SO₄ have been studied. Both compounds inhibit the corrosion of zinc in H₂SO₄ medium. Their inhibition efficiency is most affected by concentration of H₂SO₄ and temperature. A graduation in thermodynamic parameters of adsorption (ΔH_{ads} , ΔG_{ads} , and E_a) of norfloxacin and sparfloxacin was observed between H₂SO₄ concentration range of 0.01-0.03M and 0.03-0.05M respectively. Although activation energies of norfloxacin and sparfloxacin inhibited corrosion reaction of zinc were positive and greater than activation energy of uninhibited corrosion reaction of zinc, a significant statistical differences ($P \leq 0.05$) was observed between the values of E_a obtained for norfloxacin and sparfloxacin. Correlation between the two set of data was also weak. Values of ΔH_{ads} and ΔG_{ads} were negative for both inhibitor and were also found to be significantly difference from each other.

© 2008 Trade Science Inc. - INDIA

KEYWORDS

Inhibition of zinc corrosion;
Norfloxacin;
Sparfloxacin.

INTRODUCTION

In our laboratory, we have found that norfloxacin and sparfloxacin are good inhibitors for zinc corrosion. Inhibition efficiency of this compound has been attributed to the presence of heteroatoms in their electron rich aromatic chains^[1-3]. In addition several factors affects inhibition efficiency of a given inhibitor including, temperature, presence or aggressive ions, concentration of corrodent, acidity(pH), concentration of inhibitors, etc.^[4-7]. Our present study is aimed at investigating inhibitive action of norfloxacin and sparfloxacin in H₂SO₄ medium.

MATERIALS AND METHODS

Materials

The samples (norfloxacin and sparfloxacin) were synthesized by chemical method as reported by Ferrera et al.,^[3]. Zinc specimens used for the study were of dimension, 5×4×0.11cm. The acid solutions (H₂SO₄) were prepared from analar grade (manufactured by BDH chemicals). Double distilled water was used for all preparations. The concentration range of inhibitor employed was 10⁻³-5×10⁻³M. These were separately dissolved in 0.01, 0.02, 0.03, 0.04 and 0.05M.

Full Paper

Weight loss measurement

Weight loss measurements were carried out as described in literature^[10-15]. The volume of solution used was 150ml. A maximum immersion time was 168hours. Solutions were not stirred but specimens were removed from their respective solution after every 24hours of immersion. They were washed in 5% chromic acid solution (containing 1% silver nitrate in 10% aluminum chloride solution), rinsed in boiling water and dried in acetone before weighing to the nearest 4 decimal place.

From weight loss measurement, inhibition efficiency and degree of surface coverage were calculated using equation 1 and 2^[10-12]:

$$\text{Inhibition efficiency}(\%) = (1 - W_1/W_2) \times 100 \quad (1)$$

$$\text{Degree of surface coverage}(\theta) = (1 - W_1/W_2) \quad (2)$$

where W_1 and W_2 are weight losses (g/dm^3) of zinc in the presence and absence of A respectively.

RESULTS AND DISCUSSION

Effect of concentrations

Figure 1-2 show plots of weight loss versus immersion time for the corrosion of zinc in 0.01-0.05M H_2SO_4 in the presence of 0.0001-0.0005M norfloxacin and sparfloxacin at 303K. Figure 4 shows a plot of weight loss versus immersion time for the corrosion of zinc in 0.01 -0.05M H_2SO_4 , weight losses of zinc in the presence and absence of the inhibitors are found to vary with the concentration of H_2SO_4 and temperature. However values of weight losses obtained in the absence of inhibitors are higher than values obtained in the presence of inhibitors indicating that these compounds in-

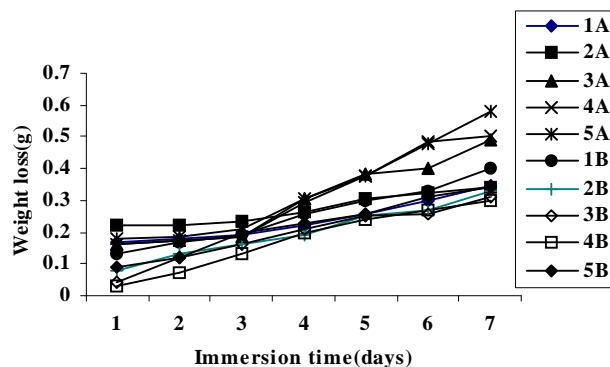


Figure 1a: Variation of weight loss with immersion time for the corrosion of zinc in 0.01M(A) & 0.02M(B) acid in the presence of 0.0001-0.0005M norfloxacin

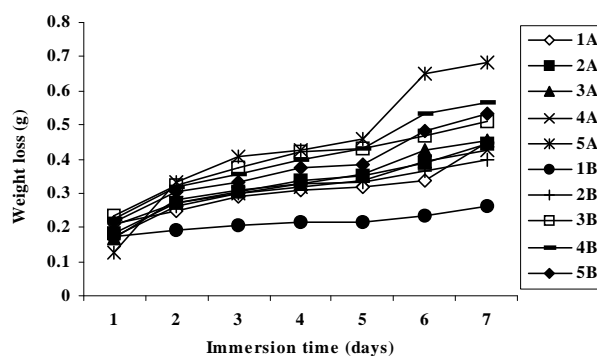


Figure 1: Weight loss versus immersion time for the corrosion of zinc in 0.01M(A) & 0.02M(B) in the presence of 0.0001-0.0005M(1-5) sparfloxacin at 303K

hibit the corrosion of zinc. Lines on the respective plot were close and parallel to each other implying that they follow similar corrosion mechanism. In the presence of inhibitors, weight losses were found to decrease with inhibitors concentration (in most cases) indicating that inhibition efficiency of the used compounds decreases with concentration. At H_2SO_4 concentration ranges of

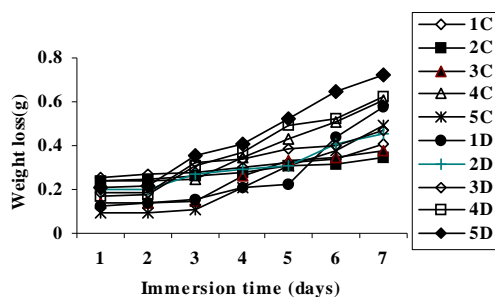


Figure 2a: A plot of weight loss versus immersion time for the corrosion of zinc in 0.03M(C) & 0.04M (D) in the presence of 0.0001-0.0005M(1-5) norfloxacin

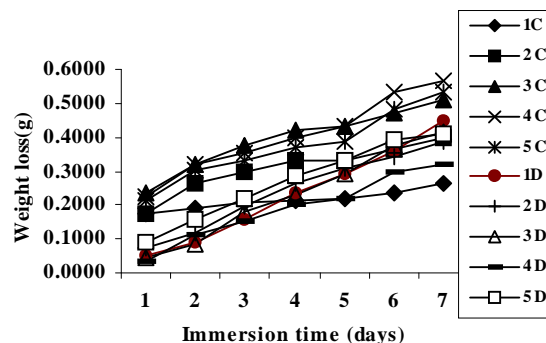


Figure 2: Variation of weight loss with immersion time for the corrosion of zinc in 0.03M(C) & 0.04M(D) in the presence of 0.0001-0.0005M(1-5) of norfloxacin at 303K

0.01-0.03M and 0.03-0.04M, were relatively far from each other for norfloxacin and sparfloxacin respectively. At 313 and 323K, weight losses were also found to increase with immersion time and follows trend corresponding to the respective compounds at similar concentration and temperature of 303K. However, values of weight losses were generally low at these 313 and 323K indicating that inhibition efficiency of these compounds increases with temperature, a character common to chemical adsorption species.

Kinetics consideration

Corrosion reactions of zinc in 0.01-0.05M H₂SO₄ in the absence and presence of the two inhibitors were found to follow first order kinetics, indicating that the fraction of zinc that corrodes increases exponentially with time according to equation 3

$$[\text{Zn}]/[\text{Zn}]_0 = -K_1 t \quad (3)$$

Where [Zn]₀ and [Zn] are the concentrations of zinc at time t=0 and at time, t. K₁ is the first order rate constant. Rearranging equation 3 4 is obtained:

$$-\log\{[\text{Zn}] - [\text{Zn}]_0\} = K_1 t / 2.303 \quad (4)$$

Plotting of Log[weight loss] versus time (Figures not shown) produces straight lines for both norfloxacin and sparfloxacin implying that first order kinetic is obeyed. From slopes of the kinetic plots, values of K₁ calculated were used to calculate values of half life at different concentrations of norfloxacin and sparfloxacin (Values not indicated) using equation 5^[10-12]:

$$t_{1/2} = 0.693/K_1 \quad (5)$$

Calculated values of half life for inhibited corrosion reaction of zinc ranged from 54-150 days and were higher than values obtained for the respective blank (which ranged from 0.678-1.5 days) implying that norfloxacin and sparfloxacin extend the half life of zinc corrosion in H₂SO₄ medium.

Thermodynamics and adsorption considerations

In order to study the effect of temperature on the corrosion reaction of zinc in H₂SO₄ in the presence and absence of sparfloxacin and norfloxacin, Arrhenius equation was used^[4-9]:

$$K = A \exp(-E_a/RT) \quad (6)$$

where K is the rate constant obtained from equation 4, A is Arrhenius or pre-exponential constant, E_a is the activation energy, R is the gas constant and T is the temperature.

Taking logarithm of both sides of equation 6, equation 7 is obtained:

$$\text{Log}K = \text{Log}A + E_a / 2.303RT \quad (7)$$

Plotting of respective values of K for norfloxacin and sparfloxacin yielded straight lines representing Arrhenius plot for the respective inhibitor at different temperatures. From slopes of lines on each plot, values of E_a were calculated. Calculated values of E_a (TABLE 1) for inhibited corrosion reactions of zinc in the presence of sparfloxacin and norfloxacin were positive and

TABLE 1: Values of thermodynamic parameters for the adsorption of norfloxacin and sparfloxacin on zinc surface

| Activation energy | | | Thermodynamic parameters of norfloxacin | | | |
|-----------------------|--------------------------------------|------------|---|------|----------------------------|---------------------------|
| Con. (M) of inhibitor | E _a (J/mol) | | Con.(M) of acid | T(K) | ΔG _{ads} (KJ/mol) | ΔH _{ads} (J/mol) |
| | 0.02M H ₂ SO ₄ | Sparf Norf | | | | |
| 0.001 | -41.3329 | 43.6229 | 0.01 | 303 | 33.3260 | -34.0520 |
| | | | | 313 | 41.4361 | |
| | 323 | 39.3930 | | | | |
| | 303 | 34.2250 | | | | |
| | 313 | 36.3595 | | | | |
| 0.002 | -42.1429 | 71.3557 | 0.02 | 323 | 43.1827 | -39.9700 |
| | | | | 303 | 34.2250 | |
| | 313 | 36.3595 | | | | |
| | 323 | 43.1827 | | | | |
| | 303 | 35.6347 | | | | |
| 0.003 | 70.2336 | 16.951 | 0.03 | 313 | 40.0263 | -36.4110 |
| | | | | 323 | 43.1827 | |
| | 303 | 16.4855 | | | | |
| | 313 | 14.4897 | | | | |
| | 323 | 15.4960 | | | | |
| 0.004 | 60.3729 | 136.2511 | 0.04 | 313 | 14.4897 | -16.8420 |
| | | | | 323 | 15.4960 | |
| | 303 | 24.9756 | | | | |
| | 313 | 19.3348 | | | | |
| | 323 | 14.5098 | | | | |
| 0.005 | -21.2552 | 6.8221 | 0.05 | 303 | 24.9756 | -25.5190 |
| | | | | 313 | 19.3348 | |
| | 323 | 14.5098 | | | | |
| | 303 | 31.5795 | | | | |
| | 313 | 37.3811 | | | | |
| 0.001 | 75.074 | 18.9269 | 0.01 | 323 | 39.3930 | -88.6850 |
| | | | | 303 | 34.6131 | |
| | 313 | 40.0263 | | | | |
| | 323 | 41.4363 | | | | |
| | 303 | 35.6347 | | | | |
| 0.002 | 45.6506 | 19.7905 | 0.02 | 313 | 40.0263 | -70.2550 |
| | | | | 323 | 41.4363 | |
| | 303 | 35.6347 | | | | |
| | 313 | 36.3595 | | | | |
| | 323 | 39.1276 | | | | |
| 0.003 | 47.2571 | 8.239 | 0.03 | 303 | 37.3811 | -17.6590 |
| | | | | 313 | 40.0263 | |
| | 323 | 41.4363 | | | | |
| | 303 | 37.3811 | | | | |
| | 313 | 47.9627 | | | | |
| 0.004 | 30.5952 | 19.9571 | 0.04 | 323 | 41.4363 | -24.578 |
| | | | | 303 | 37.3811 | |
| | 313 | 47.9627 | | | | |
| | 323 | 41.4363 | | | | |
| | 303 | 37.3811 | | | | |
| 0.005 | 34.9474 | 4.5226 | 0.05 | 313 | 37.3811 | -38.1950 |
| | | | | 323 | 41.4363 | |
| | 303 | 37.3811 | | | | |
| | 313 | 37.3811 | | | | |
| | 323 | 37.3811 | | | | |

Full Paper

higher than values obtained for the respective blank implying that norfloxacin and sparfloxacin retards the corrosion of zinc in H_2SO_4 . However, values obtained for norfloxacin (at H_2SO_4 concentration of 0.01 and 0.02M) were greater and significantly difference from values obtained for norfloxacin ($P=0.05$). At H_2SO_4 concentrations of 0.03, 0.04 and 0.05M, the reverse was also true. These trends suggests that the retarding ability of the two inhibitors depends on the concentration of H_2SO_4 . Correlation between E_a values for norfloxacin and sparfloxacin at different concentrations were weak ($r=0.2031, 0.2864, -0.68677$ and 0.0503 for H_2SO_4 concentrations of 0.01, 0.02, 0.03, 0.04 and 0.05M respectively). Confirming that norfloxacin and sparfloxacin exhibit different retarding strength for the corrosion of zinc in 0.01 -0.05M H_2SO_4 .

Values of degree of surface coverage calculated for orfloxacin and sparfloxacin from equation 2 were used to fit curves for different adsorption isotherms including lagmuir, Freundlich, Florry Huggins, Frumkin and Temkin isotherms. Lagmuir adsorption isotherm was best applicable for the adsorption of norfloxacin and sparfloxacin on zinc electrode. According to Lagmuir isotherm, the surface coverage(θ) is related to te concentration of the inhibitor in the bulk solution by equation 7^[16-20]:

$$\theta = kC / (1 + kC) \quad (8)$$

where k is the equilibrium constant for the adsorption process. Rearrangement of equation 8 gives equation 9:

$$C/\theta = 1/k + C \quad (9)$$

By plotting C/θ versus C for norfloxacin and sparfloxacin at 303-323K, straight lines (Figure 10 and 11) were obtained (with R^2 values ranging from 0.8897-1.000 for norfloxacin and from 0.8767-1.000 for sparfloxacin) indicating that norfloxacin and sparfloxacin are adsorbed on zinc electrode according to the Lagmuir adsorption isotherm. In both cases, lines on the respective isotherms were very close to each other indicating that the mechanism of adsorption of different concentrations of norfloxacin and sparfloxacin are similar. Intercepts of lines on Lagmuir plot leads to values of equilibrium constant (k).

The equilibrium constant, k for the adsorption of norfloxacin is related to free energy of adsorption (ΔG_{ads}) according to equation 10^[13-15]:

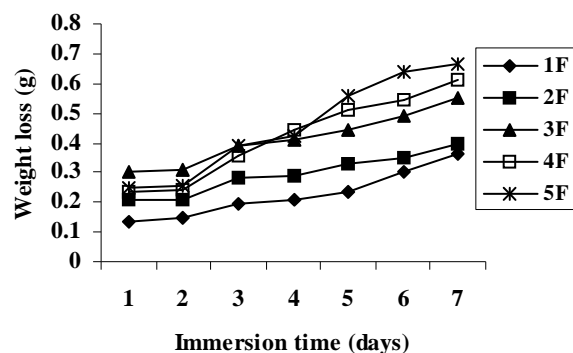


Figure 3a: A plot of weight loss versus immersion time for the corrosion of zinc in 0.05M(F) acid in the presence of 0.0001-0.0005M (1-5) norfloxacin at 303K

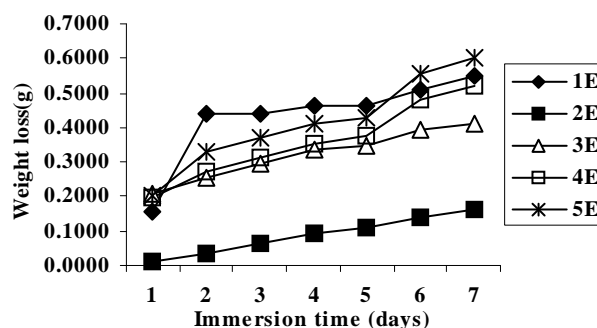


Figure 3: A plot of weight loss versus immersion time for the corrosion of zin in 0.05M(D) acid in the presence of 0.0001-0.0005M (1-5) of sparfloxacin at 303K

$$\Delta G_{ads} = -2.303RT \log(55.5k) \quad (10)$$

Values of the free energy of adsorption (TABLE 1) of norfloxacin and sparfloxacin on zinc electrode (immersed in 0.01-0.03M) were nearer to 40KJ/mol (in most cases) indicating that inhibition of zinc corrosion by norfloxacin and sprafloxacin is govern by chemical adsorption^[2]. The negative values of ΔG_{ads} indicates spontaneous adsorption of norfloxacin and sprafloxacin on the zinc surface^[6-7]. For norfloxacin, at H_2SO_4 concentration of 0.01-0.03M, the inhibition process is much favoured as the temperature increases indicating that chemical adsorption of norfloxacin on zinc electrode dominate. But for sparfloxacin, the reverse was the case except at H_2SO_4 concentrations of 0.04 and 0.05M. A significant difference between values of free energy of adsorption for both inhibitors was observed ($P \geq 0.05$). Also, correlation between them was weak ($r = 2.8017$) indicating that the magnitude of adsorption behaviour of sparfloxacin significantly differ from that of norfloxacin.

The enthalpy of adsorption can be calculated from

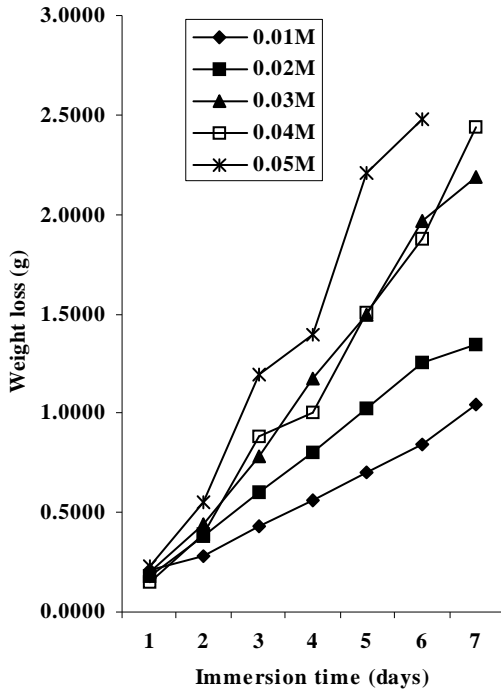


Figure 4: A plot of weight loss versus immersion time for the corrosion of zinc in 0.01-0.05M tetraoxosulphate (VI) acid at 303K

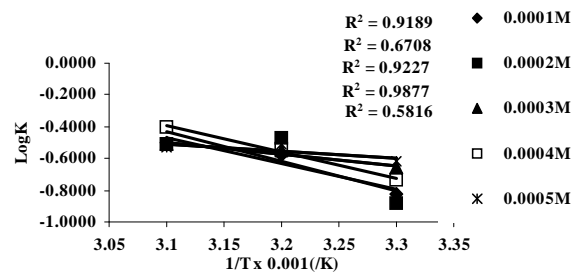


Figure 6a: Arrhenius plot for the corrosion of zinc in 0.02M acid in the presence of norfloxacin

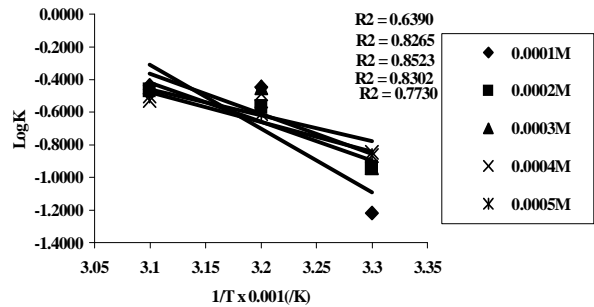


Figure 6: Arrhenius plot for the corrosion of zinc in 0.02M acid in the presence of sparfloxacin

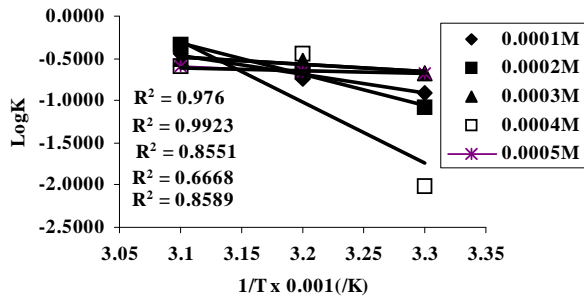


Figure 5a: Arrhenius plot for the corrosion of zinc in 0.01M acid in the presence of norfloxacin

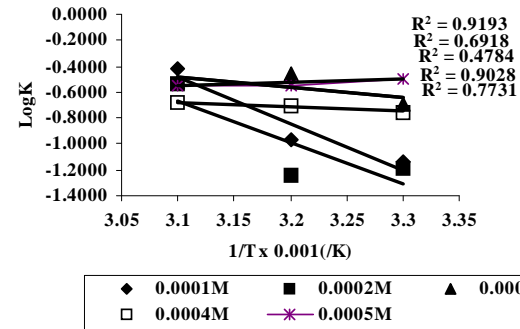


Figure 7a: Arrhenius plot for the corrosion of zinc in 0.03 M acid in the presence of norfloxacin

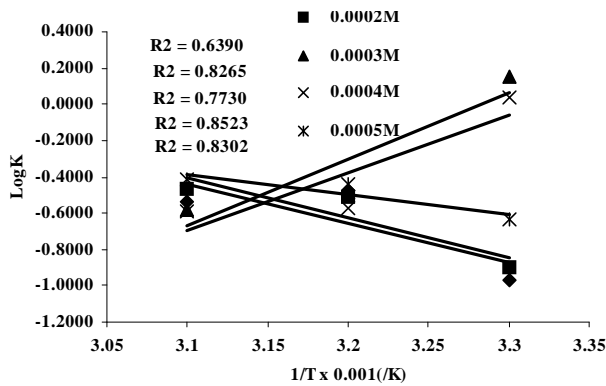


Figure 5: Arrhenius plot for the corrosion of zinc in 0.01M acid in the presence of sparfloxacin

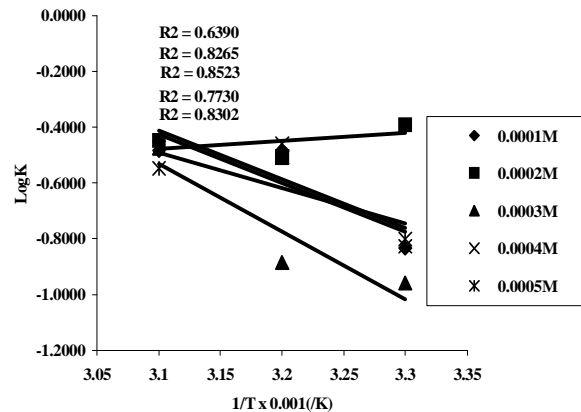


Figure 7: Arrhenius plot for the corrosion of zinc in 0.03M acid in the presence of sparfloxacin

the Gibb-Helmholtz equation (6):

Full Paper

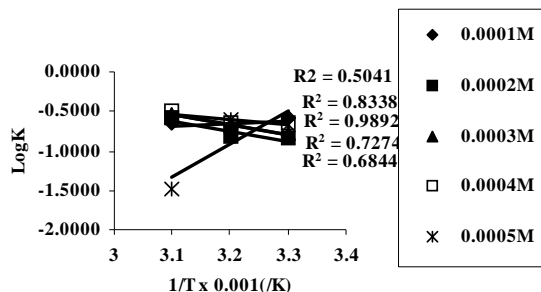


Figure 8a: Arrhenius plot for the corrosion of zinc in 0.04 M acid in the presence of norfloxacin

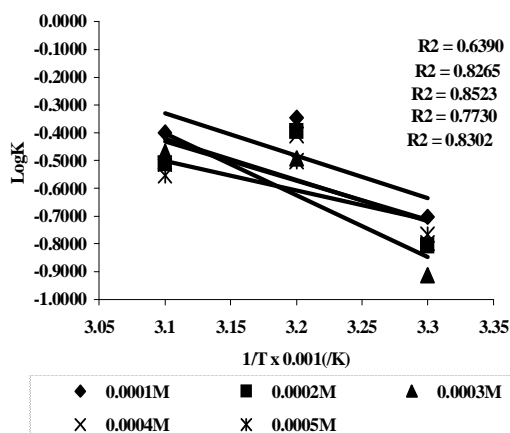


Figure 8: Arrhenius plot for the corrosion of zinc in 0.04M acid in the presence of sparfloxacin

$$[\delta(\Delta G_{\text{ads}}/T)]/\delta T = \Delta H_{\text{ads}}/T^2 \quad (11)$$

Rearranging and integrating equation 11, equation 12 is obtained:

$$\Delta G_{\text{ads}}/T = \Delta H_{\text{ads}}/T \quad (12)$$

From equation 12, a plot of $\Delta G_{\text{ads}}/T$ versus $1/T$ should give a straight line with slope equal to ΔH_{ads} (Figure 12 and 13). Values of ΔH_{ads} are all negatives (TABLE 1) indicating that adsorption of norfloxacin and sparfloxacin on zinc electrode is exothermic. The magnitude of ΔH_{ads} is less negative for adsorption at H_2SO_4 concentrations of 0.04 and 0.05M (for norfloxacin) compares to adsorption at 0.01-0.05M. This indicates that norfloxacin is adsorbed more strongly at H_2SO_4 concentration of 0.01-0.03M sparfloxacin is more adsorbed at H_2SO_4 concentration range of 0.04 and 0.05M. The strength of the adsorption can further be attributed to the formation of strong electrostatic bond (at H_2SO_4 concentration of 0.01-0.03M) compares to weak bond when the concentration of H_2SO_4 is increased from 0.04-0.05M for

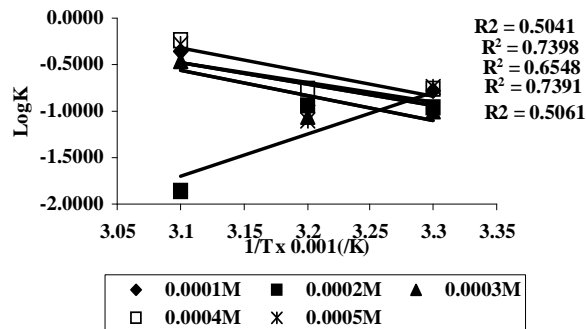


Figure 9a: Arrhenius plot for the corrosion of zinc in 0.05M acid in the presence of norfloxacin

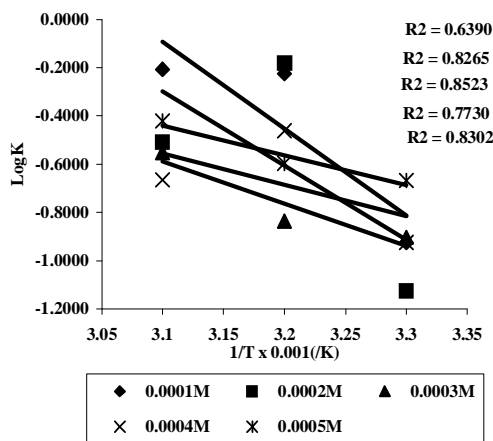


Figure 9: Arrhenius plot for the corrosion of zinc in 0.05M acid in the presence of sparfloxacin

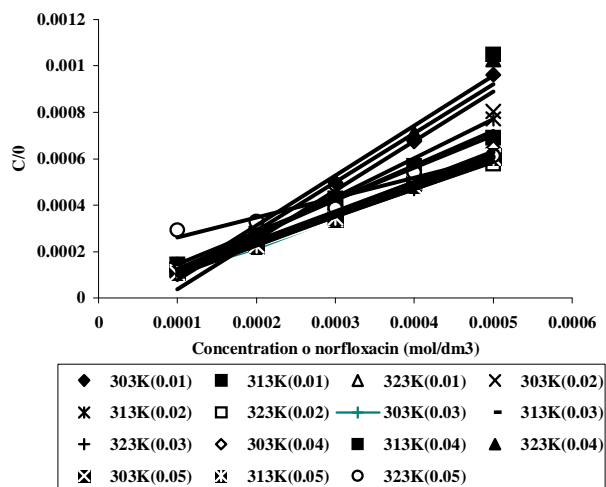


Figure 10: Curve fitting for adsorption of norfloxacin on zinc surface according to Langmuir isotherm

norfloxacin and vice versa. It is also proposed by the authors that as the concentration of H_2SO_4 increases above 0.03M, influences of acidity on solvation and adsorption of norfloxacin competes with other factors

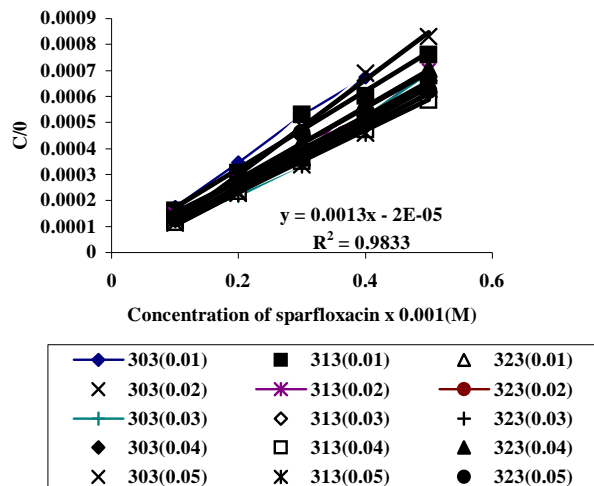


Figure 11: Curve fitting for adsorption of sparfloxacin on zinc electrode according to Langmuir

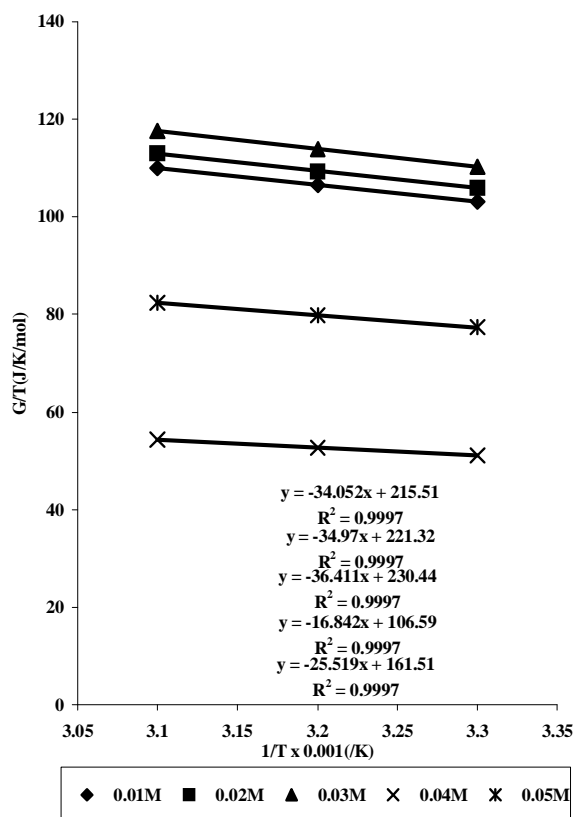


Figure 12: Variation of G/T with 1/T for norfloxacin

to weaken or strengthen the adsorption bond. Values of enthalpy of adsorption for norfloxacin significantly differ from values obtained for sparfloxacin ($P \geq 0.05$) and correlation between them was also weak ($r=0.4786$).

Inhibition efficiency and mechanism of inhibition by sparfloxacin and norfloxacin

TABLE 2: Inhibition efficiency of 0.0001-0.0005M sparfloxacin in 0.01M-0.05M H_2SO_4

| Con (mol/dm ³) | 0.01M tetraoxosulphate (VI) acid | | | 0.02M tetraoxosulphate (VI) acid | | |
|-------------------------------|-------------------------------------|-------|-------|-------------------------------------|-------|-------|
| | 303K | 313K | 323K | 303K | 313K | 323K |
| 0.0001 | 57.07 | 62.22 | 72.89 | 80.6 | 68.21 | 82.7 |
| 0.0002 | 57.66 | 64.97 | 69.8 | 70.54 | 72.64 | 83.06 |
| 0.0003 | 56.8 | 56.57 | 70.17 | 61.99 | 70.71 | 84.51 |
| 0.0004 | 59.27 | 66.42 | 70.09 | 57.89 | 77.44 | 84.51 |
| 0.0005 | 34.64 | 65.71 | 73.5 | 60.24 | 71.21 | 84.48 |
| Con (mol/dm ³) | 0.03M tetraoxosulphate (VI) acid | | | 0.04M tetraoxosulphate (VI) acid | | |
| | 303K | 313K | 323K | 303K | 313K | 323K |
| 0.0001 | 74.76 | 76.71 | 84.61 | 82.63 | 86.79 | 67.95 |
| 0.0002 | 92.55 | 76.11 | 84.15 | 76.26 | 85.2 | 68.1 |
| 0.0003 | 89.15 | 66.67 | 81.4 | 81.29 | 85.72 | 82.47 |
| 0.0004 | 76.31 | 75.82 | 81.47 | 75.64 | 84.67 | 68.76 |
| 0.0005 | 72.58 | 83.67 | 80.74 | 75.57 | 85.19 | 70.51 |
| Con (mol/dm ³) | 0.05M tetraoxosulphate (VI) acid | | | | | |
| | 303K | 313K | 323K | | | |
| 0.0001 | 88.1 | 79.03 | 76.63 | | | |
| 0.0002 | 85.87 | 87.26 | 78.32 | | | |
| 0.0003 | 82.01 | 89.18 | 65.47 | | | |
| 0.0004 | 77.88 | 87.12 | 76.81 | | | |
| 0.0005 | 79.19 | 77.54 | 80.23 | | | |

TABLE 3: Inhibition efficiency of 0.0001-0.0005M norfloxacin in 0.01M-0.05M H_2SO_4

| Con (mol/dm ³) | 0.01M tetraoxosulphate (VI) acid | | | 0.02M tetraoxosulphate (VI) acid | | |
|-------------------------------|-------------------------------------|-------|-------|-------------------------------------|-------|-------|
| | 303K | 313K | 323K | 303K | 313K | 323K |
| 0.0001 | 78.39 | 70.19 | 85.01 | 82.84 | 70.88 | 81.33 |
| 0.0002 | 85.59 | 72.40 | 82.73 | 84.56 | 75.16 | 87.73 |
| 0.0003 | 60.38 | 70.19 | 79.96 | 66.55 | 70.02 | 87.06 |
| 0.0004 | 59.18 | 70.19 | 79.58 | 72.55 | 80.30 | 82.48 |
| 0.0005 | 51.98 | 72.40 | 80.35 | 62.26 | 64.88 | 86.54 |
| Con (mol/dm ³) | 0.03M tetraoxosulphate (VI) acid | | | 0.04M tetraoxosulphate (VI) acid | | |
| | 303K | 313K | 323K | 303K | 313K | 323K |
| 0.0001 | 92.46 | 86.69 | 82.06 | 80.36 | 81.23 | 69.92 |
| 0.0002 | 94.47 | 92.87 | 83.07 | 89.09 | 82.11 | 62.19 |
| 0.0003 | 87.93 | 81.93 | 78.24 | 87.34 | 79.49 | 67.89 |
| 0.0004 | 81.40 | 85.26 | 84.92 | 80.36 | 76.43 | 56.27 |
| 0.0005 | 79.89 | 85.74 | 81.36 | 77.31 | 47.63 | 48.66 |
| Con (mol/dm ³) | 0.05M tetraoxosulphate (VI) acid | | | | | |
| | 303K | 313K | 323K | | | |
| 0.0001 | 89.93 | 95.20 | 34.30 | | | |
| 0.0002 | 91.71 | 89.09 | 61.04 | | | |
| 0.0003 | 89.09 | 86.91 | 77.83 | | | |
| 0.0004 | 83.42 | 79.92 | 74.02 | | | |
| 0.0005 | 81.67 | 82.98 | 81.64 | | | |

TABLE 2 and 3 shows inhibition efficiency of sparfloxacin and norfloxacin. Inhibition efficiencies of sparfloxacin and norfloxacin are influenced by temperature, concentration of sparfloxacin/norfloxacin and concentration of acid. On the average, inhibition efficiency

Full Paper

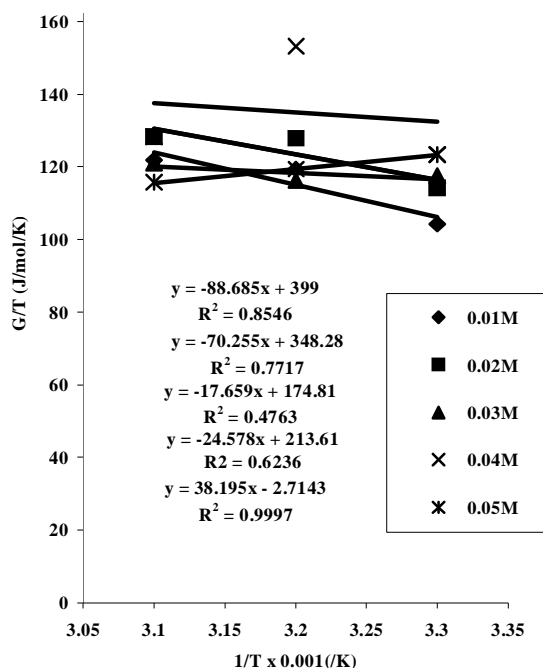


Figure 13: Variation of G/T with 1/T for sparfloxacin

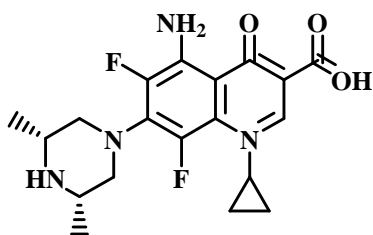


Figure 14: Chemical structure of sparfloxacin

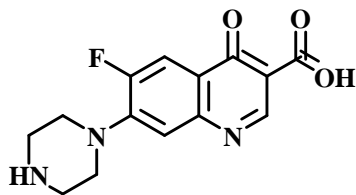


Figure 15: Chemical structure of norfloxacin

of both inhibitors increases as the concentrations of H_2SO_4 increases. Enhancement of inhibition efficiency of the studied compounds by increased concentration of tetraoxosulphate(VI) implies that adsorption of the used inhibitors is more activated at higher concentration of acid than at lower concentrations.

The molecular mass of sparfloxacin and norfloxacin are 392.41 g/mol and 319.33 g/mol respectively. A careful inspection of TABLE 2 and 3 reveals that inhibition efficiency of sparfloxacin at different temperatures and concentrations are relatively higher than corresponding

efficiencies obtained for norfloxacin. Several reasons may be responsible for the observed trend. First, inhibition efficiency of most inhibitor increases as the molar mass of the inhibitor increases^[17-20]. Secondly, the present of amino group and extra fluorine atom in sparfloxacin which are absent in norfloxacin might have enhanced electron donating effect of sparfloxacin compare with norfloxacin, which has just one fluorine atom.

From the above, the following mechanism is proposed for the inhibition of zinc corrosion by sparfloxacin and norfloxacin;

- i. In acidic medium, the inhibitors undergo dehydration to yield anhydronorfloxacin and anhydrosparfloxacin which suffers further cleavages and lactonization.
- ii. Dilute acid promotes epimerization of carbon atoms therefore, it is propose that adsorption of the inhibitors on zinc surface is stabilized by each molecule of the inhibitor donating electron to a vacant orbital of zinc.

The proposed mechanism is supported by relatively high values of activation energy, moderate values of enthalpy changes and negative values of entropy change which indicates the formation of a stabilised complex.

REFERENCES

- [1] A.O.James, N.C.Oforka, K.Abiola; Intern.J. Electrochem.Sc., **2**, 284 (2007).
- [2] S.D.Shetty, P.Shetty, H.V.S.Nayak; J.Child.Chem. Soc., **51**, 849 (2006).
- [3] A.L.O.Ferreira, R.L.C.Giordana, R.C.Giordano; Braz.J.of Chem.Engr., **4**, 529 (2004).
- [4] S.Muralidharan, R.Chandrasek, S.K.Iyer; Proc. Indian Acad.Sci., **112**, 136 (2000).
- [5] R.Solmaz, G.Kardas, B.Yaziei, M.Erbil; Protection of metals., **41**, 632 (2005).
- [6] K.C.Emregul, R.Kurtaran, O.Atakol; Corrosion Sc., **45**, 2817 (2003).
- [7] M.Ehteshamzade, T.Shahrabi, M.G.Hosseini; Appl. Surf.Sc., **252**, 2959 (2006).
- [8] G.K.Gomma, M.H.Wahdan; Mat.Chem.& Phys., **39**, 213 (1995).
- [9] H.M.A.Soliman, A.H.H.Rashman; J.Braz.Chem. Soc., **17**, 714 (2006).
- [10] E.E.Ebenso; Nigerian J.of Chem.Res., **6**, 12 (2001).
- [11] U.J.Ekpe, P.C.Okafor, E.E.Ebenso, O.E.Offiong,

Full Paper

- B.I.Ita; Bullentin of Electrochem., **17**, 135 (2001).
- [12] E.E.Ebenso, P.C.Okafor, U.J.Ekpe, U.J.Ibok, A.I. Onuchukwu; J.Chem.Soc., Nigeria, **29**, 25 (2004).
- [13] E.E.Oguzie, E.E.Ebenso; Pigment & Resin Tech., **35**, 35 (2006).
- [14] H.Ashassi-Sorkhabi, B.Shabani, B.Aligholipour, D.Seifzadeh; Appl.Surf.Sc., **22**, 4047 (2006).
- [15] H.Ashassi-Sorkhabi, B.Shaabani, D.Seizadeh, Appl. Surf.Sci., **239**, 164 (2005).
- [16] S.Bilgic, N.Caliskan; Appl.Surf.Sci., **152**, 107 (1999).
- [17] S.Ayyala, T.V.Subrahmanyam, R.J.Pugh, K.S.E. Forddberg; Mineral Eng, **6**, 929 (1993).
- [18] M.M.Attar, J.D.Scantlebury; JCSE., **8**, 97 (2005).
- [19] W.A.Monika, A.D.Siddique; Portugaliae Electro chimica acta, **23**, 455 (2005).
- [20] T.D.Talanti, M.N.Desai, N.K.Shah; Mat.Chem.& Phys., **93**, 54 (2005).