



Trade Science Inc.

April 2007

Volume 2 Issue 1

Inorganic CHEMISTRY

An Indian Journal

Full Paper

ICAIJ, 2(1), 2007 [77-80]

Synthesis Of Pentacoordinate Organic Silicon And Polyphosphazene Containing Silicon With Hydrophobic Superfine SiO₂



Corresponding Author

Xu Jian-Zhong
College of Chemistry and Environmental
Science, Hebei University, Baoding, Hebei
071002, (CHINA)
Tel: +86 0312 5079525; Fax: +86 0312 5079525,
E-mail: Xujz@mail.hbu.edu.cn

Received: 17th November, 2006

Accepted: 22th November, 2006

Web Publication Date : 7th February, 2007



Co-Authors

He Yong-Wu¹, Wang Chun-Zheng¹, Tang Ran-Xiao^{1,2}

¹College of Chemistry and Environmental Science, Hebei University,
Baoding, Hebei 071002, (CHINA)

²College of Science, Agriculture University of Hebei, Baoding,
Hebei 071001, (CHINA)

ABSTRACT

Pentacoordinate organic silicon was prepared with a new material of hydrophobic superfine SiO₂ at a much shorter reaction time and higher yield, and then it was used to react with hexachlorocyclotriphosphazene to get polyphosphazene containing silicon, the products behavior was studied with TGA and infrared spectrum. © 2007 Trade Science Inc.

-INDIA

KEYWORDS

Hexachlorocyclotriphosphazene;
Pentacoordinate organic
silicon;
Synthesis;
Thermogravimetric analysis.

INTRODUCTION

Silicon is one of the most abundance natural resources, which is very important to develop organic materials containing silicon. But the organosilicon monomers involved in these approaches are prepared exclusively from carbothermal reduction of silicon dioxide which is energy-extensive and equipment-extensive^[1]. Pentacoordinate silicon can be prepared directly from SiO₂ and ethylene glycol in the presence of KOH at about 200°C was firstly reported by Laine et al in 1991^[2], which have received extensive attention in the last decades. It has opened up many

avenues for new research in the fields of conductor materials and high-performance ceramics overseas^[3-5], and the polymers containing silicon was successfully used to the surface modification of silica white and synthesis of polyurethane containing silicon in recent years at home^[6].

In this paper, pentacoordinate organic silicon was prepared with a new material of hydrophobic superfine SiO₂, then it was used to react with hexachlorocyclotriphosphazene to get polyphosphazene containing silicon, and the products behavior was preliminarily studied with TGA and infrared spectrum.

Full Paper

EXPERIMENTAL

Materials

Hydrophobic superfine SiO_2 was industrial grade obtained from Tianjin Yuli chemical technology plant. The other reagents of glycol, potassium hydroxide, absolute methanol, chlorobenzene, pyridine, phosphor pentachloride and dioxane were all analytical grade.

Synthesis

1. Synthesis of hexachlorocyclotriphosphazene

The synthesis of hexachlorocyclotriphosphazene was according to the reference of^[7,8].

2. Synthesis of potassium glycolate silicate

The synthesis of potassium glycolate silicate was according to the reference of^[2,9,10].

3. Synthesis of polyphosphazene containing silicon

The synthesis of polyphosphazene containing silicon was according to the reference of^[9,10].

Analysis methods

1. IR spectrum

Samples were analyzed by fourier transform after potassium bromide tabulating on Vektor27 (Bruker).

2. Thermogravimetric analysis

Thermogravimetric analysis was performed at $20^\circ\text{C}/\text{min}$ on WCT-2 differential thermal analyzer under N_2 .

3. XRD

X-ray diffraction (XRD) analysis was performed at $20^\circ/\text{min}$ on D/MAX-II diffractometer equipped with graphite monochromatized Cu, the diffraction angle range is from 10° to 60° .

RESULT AND DISCUSSION

Synthesis of pentacoordinate organic silicon and polyphosphazene containing silicon

1. Synthesis of pentacoordinate organic silicon

In a three necked bottle a mixture of 6.0 g Hydrophobic superfine SiO_2 , 5.6 g KOH and 120 mL $\text{HOCH}_2\text{CH}_2\text{OH}$ was stirred magnetically under N_2 for ten minutes, and then was heated to about 200°C , standard distillation setup so that all the excess glycol

was distilled off slowly with removal of water, after thirty minutes solid product was appearing and then stopped the reaction. The solid product was kept sealing overnight and then dissolved with 100mL CH_3OH and filtered. The filtrate was precipitated with 400 mL CH_3CN , the precipitate was dried at 130°C in vacuum, the yield is about 90%.

2. Synthesis of polyphosphazene containing silicon

Hexachlorocyclotriphosphazene was recrystallized from n-heptane several times before use. 3.47 g HCCP was dissolved in 10 mL dioxane and added dropwisely into 60 mL solution of potassium glycolate silicate in methanol under refluxing in the presence of nitrogen. Then the mixture was agitated vigorously to react until the solution reached neutrality. The reaction mixture was filtered to remove the white precipitate and dried at 130°C in vacuum. The obtained primrose powder was polyphosphazene containing silicon.

Structure analysis

1. XRD spectrum of the white precipitate

X-ray diffraction (XRD) analysis of the white precipitate and pure KCl in analytical reagent grade were performed. The results were shown in figure 1. Comparing (a) and (b), it is sure that the precipitate is KCl. Thus we can conclude that pentacoordinate silicon has replaced the chlorine in hexachlorocyclo-

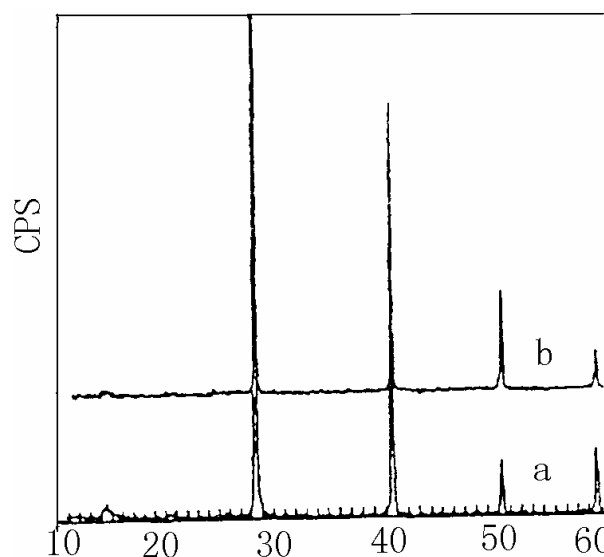


Figure 1: XRD spectrum (a) pure KCl (b) the white precipitate

triphosphazene.

2. IR spectrum of the product

Figure 2 is the IR spectrum of the product. In figure (a), the band at 3388cm^{-1} was caused by the vibration of OH^- group, the band at 2855cm^{-1} was assigned to the vibration of $-\text{CH}_2-$ group, and the bands at 1093cm^{-1} and 1040cm^{-1} were attributed to Si-O-C group and the C-O group joining with $-\text{OH}$, the above data is consistent with the reference^[9]. Comparing figure (b) with (a) and (c), we can find after reaction, the most strong absorption peaks of P=N shifted to higher wavenumber from 1169cm^{-1} and 1215cm^{-1} to 1331cm^{-1} and 1425cm^{-1} , the bands at 522 and 603cm^{-1} attributed to the vibration of pCl group disappeared, the bands of Si-O-C and P-O-C overlapped at 1082cm^{-1} . From the figure (b) we also find $-\text{CH}_2-$, the bands at 2952cm^{-1} and 2860cm^{-1} were assigned to the groups of $-\text{CH}_3$ and, the bands at 1082cm^{-1} and 970cm^{-1} were caused by the vibration of P-O-C group, the peak at 3418cm^{-1} was attributed to the vibration of OH^- group. From the above results we can conclude that pentacoordinate organic silicon has substituted the chlorine in hexachlorocyclotriphosphazene and some of silicons have connected to the phosphazene ring.

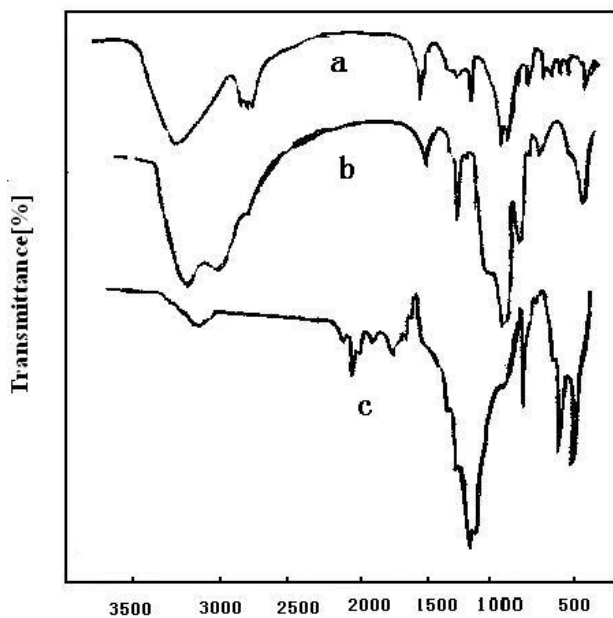


Figure 2: IR spectrum of the product (a) pentacoordinate organic silicon (b) polyphosphazene containing silicon (c) hexachlorocyclotriphosphazene

Thermogravimetric analysis of the product

Figure 3 shows the results of TG and TGA analysis of polyphosphazene containing silicon. There are three apparent mass loss processes. The initial 5.4% at 79.9°C mass loss corresponds to the volatilization of small molecules such as methanol, dioxane and so on. The second mass loss period at about 253.8°C is ascribed to the decomposition of the phosphazene ring to give off ammonia or the other nitride, and the amount of mass loss is 19%. The third mass loss is at 346.7°C with the amount of mass loss 11%, this process corresponds to the carbonization of the residue. But the product will do on decomposing and

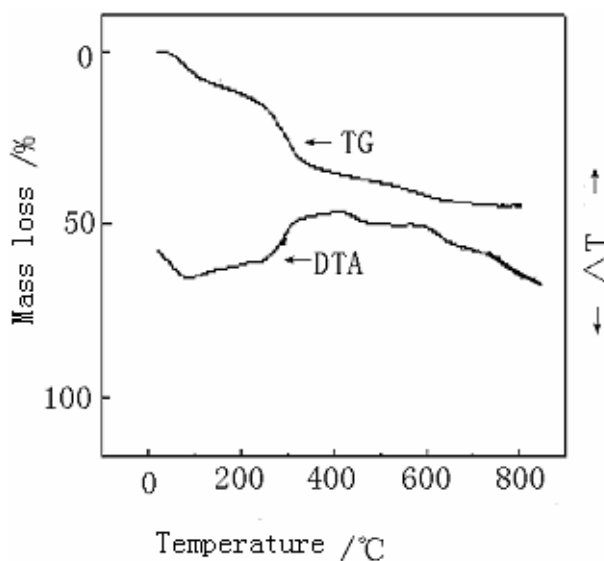


Figure 3: TGA of the product

losing until 711.3°C , the ultimate residue of the product is 55.0%. This result is consistent with the report of Liu and Matyjaszewski^[9-11].

CONCLUSIONS

Pentacoordinate organic silicon was synthesized with a new material of hydrophobic superfine SiO_2 at a much shorter time and higher yield comparing with that of silica. The obtained pentacoordinate organic silicon was reacted with hexachlorocyclotriphosphazene to get polyphosphazene containing silicon, the results of analysis of TGA show that the product has good thermal stability which can open up many avenues for new research in the field of flame retardants containing silicon.

REFERENCES

- [1] K.Y.Blohowiak, M.L.Hoppe, R.M.Laine; Chem. Mater., **6(11)**, 2177 (1994).
- [2] R.M.Laine, K.B.Youngdahl, T.R.Robinson; Nature, **353**, 642 (1991).
- [3] C.Chuit, R.J.P.Corrius, R.M.Reye; Chem. Rev., **93**, 1371 (1993).
- [4] R.M.Laine, R.T.Dvid, L.M.Brian; Chem.Mater., **8**, 1952 (1996).
- [5] P.Kansal, R.M.Laine; J.Am.Ceram.Soc., **77**, 875 (1994).
- [6] W. X.Wang, K.C.Gong; Aging and Application of Synthetical Materials(Hecheng Cailiao Laohua yu Yingyong), **(2)**, 1 (2000).
- [7] J.Z.Xu, Y.W.He et al; J of Hebei University (Hebei Daxue Xuebao), **(2)**, 64 (2006).
- [8] J.Z.Xu, Y.W.He et al; Chemical Research in Chinese Universities, **21**, 65 (Supplement) (2005).
- [9] Y.F.Zhang, K.C.Gong et al; Synthesis and Aaging of Materials (Hecheng Cailiao yu Laohua), **4**, 1 (2000).
- [10] Y.F.Zhang, A.H.Liu et al; J.Mater.Sci.Lett., **20**, 789 (2001).
- [11] G.Kickelbick, P.J.Miller, K.Matyjaszewski; MRS Res.Soc.Symp.Proc., **576**, 126 (1999).