



Trade Science Inc.

Materials Science

An Indian Journal

Full Paper

MSAIJ, 8(5), 2012 [193-198]

The effect of fly ash on resistance of hardened cement pastes to sodium chloride attack

E.Al-Salami

Faculty of Science, King Khalid University, Abha, (SAUDIARABIA)

E-mail : aeslami@kku.edu.sa

Received: 7th December, 2011 ; Accepted: 4th January, 2012

ABSTRACT

This paper investigated the influence of sodium chloride solution (NaCl) on the physical properties of cement pastes incorporating fly ash as compared with plain cement pastes. The ordinary Portland cement was partially substituted with 35% fly ash (class F) by weight. The blended cement specimens were prepared using the standard water of consistency. Cement paste samples hydrated for 3, 14 and 28 days were immersed in NaCl solutions with different concentrations ranging from 0.5% up to 1.5%. The effect of NaCl attack on bulk density, porosity, chemically bound water, relative expansion and loss of weight was studied using the standard techniques. The results showed that, cement pastes incorporating fly ash are characterized by high resistance to chloride attack that plain cement, the porosity of fly ash – cement pastes are less than that of plain cement pastes.

© 2012 Trade Science Inc. - INDIA

KEYWORDS

Blended cement;
Fly ash;
Bulk density;
Porosity;
Bound water;
Weight loss;
Relative expansion.

INTRODUCTION

The chloride ions are one of substances that cause damage of the passive protection of steel reinforcement inside the concrete^[1]. These chlorides can be found in the concrete from the moment of mixing, or after the use (sources are, sea water or groundwater). And the presence of chlorides - whatever their sources - in the concrete leads to stimulate the process of corrosion. The free chloride ions attack the reinforcing steel and cause it to rust. Mechanical and chemical reactions in this case are highly complex, but we can easily say that the chloride ions are able to disrupt the interactions which occur on the surface of reinforcing steel which provides a passive protection. Because the degree of

influence of chlorides on the properties of concrete related to its ability to penetrate into the concrete so it is important and necessary to use mineral additives to reduce permeability and increase the resistance of concrete against chlorides attack, which works to improve the performance and extend the life time of concrete structures. The use of pozzolans which reacts with free lime (calcium hydroxide) which results during the hydration of cement and converting it into calcium silicates and aluminates hydrates which working to fill the gaps and the internal capillary pores inside cement matrix^[2,3]. Examples of pozzolana materials are silica fume which are characterized by high surface area (about four times the surface area of cement, 20.000 cm²/g). Silica fume is a byproduct in the manufacture of alloys of sili-

Full Paper

con and ferrosilicon alloys, it interacts with calcium hydroxide comprising calcium silicate hydrate which typically deposits in the pore system and improve microstructure. other materials are fly ash as well as blast furnace slag^[4]. This research aims to study the effect of sodium chloride salts attack on physical properties (such as bulk density - porosity) of cement paste mixed with fly ash in order to determine the effect of fly ash on cement resistance to chlorides.

EXPERIMENTAL WORK

The starting materials used in this study were ordinary Portland cement of Blaine surface area ~ 3100 cm²/g and fly ash (FA) of Blaine surface area ~3000 cm²/g. Figure (1) shows the SEM micrograph of class F-Fly ash.

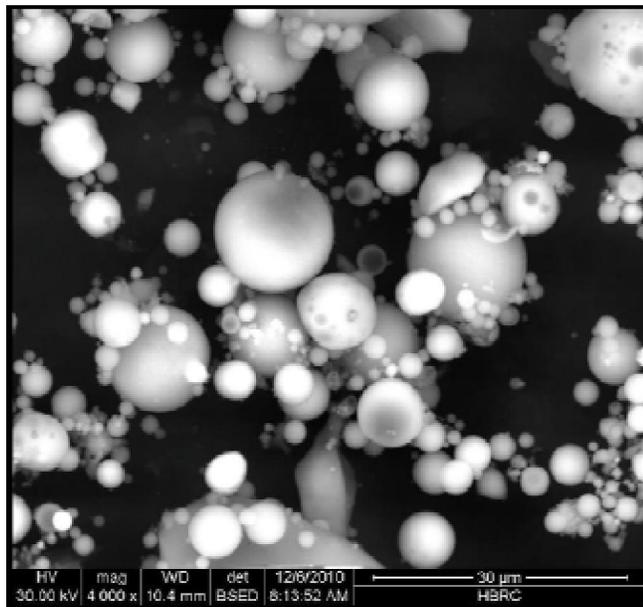


Figure 1 : SEM micrograph of fly ash

The oxide composition of OPC and fly ash were introduced in TABLE (1). The blended cement pastes were prepared using ordinary Portland cement that was partially substituted by 35% by weight of cement. The ingredients were homogenized on a roller in a porcelain ball mill with four balls for 1 hour to assure complete homogeneity. The pastes were prepared using the water/cement ratios 0.3. The pastes were molded into 2*2*2 cm cubes. The moulds were vibrated for one minute to remove any air bubbles. The samples were kept in moulds at 100% relative humidity for 24 hours,

and then it cured under water for 3, 14 and 28 days. The hardened cement pastes were dried at a temperature of 105°C for 24 hours in an oven, Then, they were kept in sodium chloride (NaCl) solution of concentration 5000,10000 and 15000 ppm for 3, 14 and 28 days. Each measurement of the physical properties was carried out for three identical cubes of the same mix composition. The bulk density and absorption of prepared samples were measured according to ASTM C220^[8].

TABLE 1 : Chemical analysis of the starting materials

Constituents, (%)	OPC	Fly ash
CaO	62.56	1.48
SiO ₂	20.85	70.72
Al ₂ O ₃	4.70	16.48
Fe ₂ O ₃	3.86	5.59
MgO	1.23	1.09
SO ₃	2.79	1.18
Na ₂ O	0.49	0.27
K ₂ O	0.12	0.44
I. Loss	2.82	2.73

Determination of density and porosity

The specimens were Immersed in water at room temperature (22°C) for 24 h. The specimens Weights were recorded while suspended and completely submerged in water. The specimens were Removed from water and water allowed to drain for 1 min by placing specimens on a wire mesh, visible surface water were removed with a damp cloth the saturated weight was determined and recorded as W_s. All specimens were dried in a ventilated oven at 105°C for not less than 24 h and two successive weightings were record at intervals of 2 h until an increment of not greater than 0.2% of the last previously determined weight of the specimen. The weight of dried specimens were Recorded as W_d (oven-dry weight). The absorption and oven-dry density were calculated as:

$$\text{Absorption\%} = [(W_s - W_d)/W_d] \times 100];$$

$$\text{Density (Kg/m}^3\text{)} = (W_d/(W_s - W_i) \times 1000$$

Where W_i, W_s, W_d are in kg

$$\text{loss of weight (Lw); Lw}=(W_d-Ig)/W_d \times 100$$

Where Ig is the weight after ignition (g).

$$\text{Combined water (Wn); Wn} = [W_d - W' / W'] - L$$

Where W' : is the weight after ignition for one hour

(g) at 1000°C then cooled in a desiccators and weighted again. L ; is the ignition loss of unhydrated specimen; $L = (W' - W_{1000^\circ\text{C}})$.

RESULTS AND DISCUSSION

The physical properties of cement pastes subjected to different concentrations of NaCl solution were studied to clarify its physical performance affected during sodium chloride exposure. The results of bulk density of the hardened cement pastes, which exposed to different concentrations of NaCl in absence and presence of FA are graphically shown in Figure (2-a, b). In general, the bulk density increases gradually with increasing, the hydration age of the cement pastes. This is due to the decrease in the total porosity with increasing hydration age as a result of the filling of pores by the hydration products. The results of Figure (2-a) indicate that the bulk density of the hardened cement pastes increases at concentration ~ 5000 ppm of NaCl, then decreases gradually with increasing of NaCl. The bulk density of blended cement pastes containing 35% FA increases as the concentration of sodium chloride increases. The increase of the bulk density is mainly due to the activation of blended cement with chloride ions in the samples forming hydrated products which fill some open pores in the samples^[5]. Figures (3-a, b) shows the variation in the mass loss versus the concentration of NaCl at different curing ages. It is clear that the rate of mass loss decreases with increasing the curing age due to the precipitation of hydrated phases in to the available pores of cement pastes but in Figure (3-a) the rate of the of mass loss increases with the concentration of NaCl in the samples, the larger amount of mass loss is caused by surface scaling.

In Figure (3-b) the rate of the mass loss decreases with increasing of NaCl in the samples that is due to the FA reacts with the liberated lime from the hydration of clinker, hence the free lime is nearly consumed. So there is no chance to reaction of lime with chloride group. The total porosity of the blended cement pastes cured for 3, 14 and 28 days are graphically represented as a function of the concentration of NaCl in the samples in Figure (4-a, b). It is clear that the total porosity decreases with curing time for all hardened cement pastes. This is due to the filling up of a part of the available pore

volume with the hydration products, as the hydration proceeds^[10]. In Figure (4-a) the total porosity decreasing up to 5000 ppm, then increasing with the concentration of NaCl in the samples. This variation mainly depending on the rate of the geometrical random arrangement of the material hydrated phases during the hydration mechanism inside the matrix of the sample^[6]. The increase in the total porosity values of hardened blended cement pastes after the concentration ~ 5000 ppm is related to interaction of chloride with liberated lime from the hydration reaction forming what is known as hydrocalumite ($\text{C}_3\text{A} \cdot \text{CaCl}_2 \cdot 10\text{H}_2\text{O}$) causing softening to the composition with formation of hydration products with a weaker microtexture and a globally more porous cement paste^[1,3]. The variation of the total porosity in Figure (3-b) is decreasing with increasing of NaCl in the blended specimens. That is due to the formation of much amounts of (C-S-H) pozzolanic reaction of FA with CH, also the content of FA in the opc matrix to decrease the interaction of the liberated lime (C-H) with the chloride to form hydrocalumite, which increasing the total porosity^[9]. The relative expansion of the blended cement pastes as a function in the concentration of the NaCl and at different curing times were represented in Figure (5-a, b). The general behavior of the relative expansion is decreasing with increasing the curing time due to the precipitation of hydrated phases into the pores of the system, and that is leading to decreasing in the relative expansion of the samples. In Figure (5-a) the relative expansion increasing with increasing the concentration of NaCl in the sample, and that is attributed to the ingress of chloride ions into the cement matrix through the open pores. But in Figure (5-b) the relative expansion decreasing with increasing NaCl in the samples after the concentration ~ 5000 (ppm), and that is due to the random arrangement of the hydrated phases in the cement matrix. The decreasing in the relative expansion with NaCl is mainly due to the increase of the FA hydration, in the cement matrix, chemical combined water for plain and blended cement pastes as a function in the concentration of the NaCl and at different curing times are graphically represented as a function in the concentration of NaCl in Figure (6-a, b). In general in this Figure (6-a, b) the chemical combined water increases with the curing time, and that is related to the progress of hydration reactions with curing time,

Full Paper

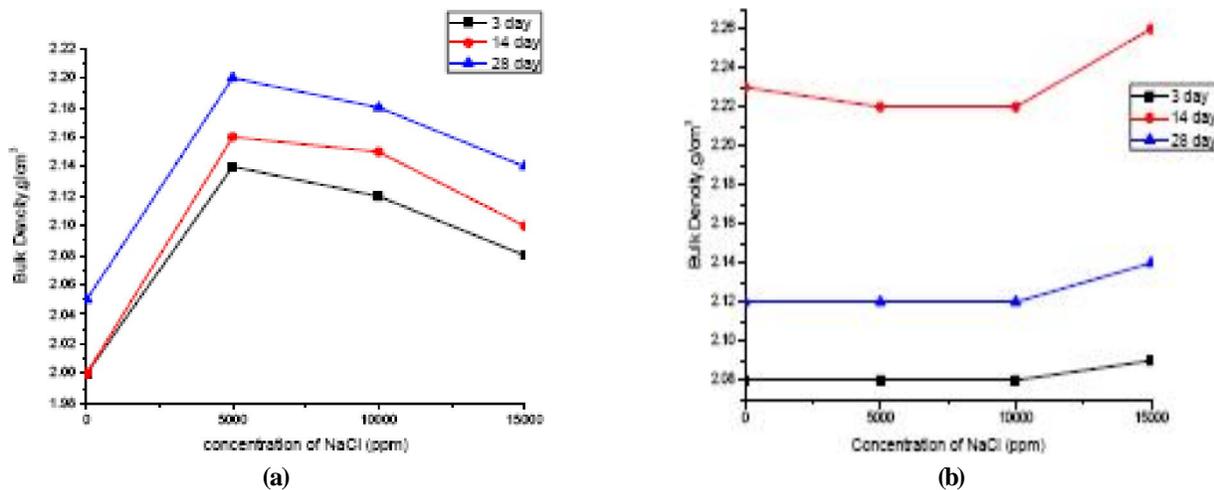


Figure 2 : (a, b) variations of bulk density of the hardened cement pastes with the concentration of NaCl at different curing times, (a) Plain cement paste, (b) Fly ash – Cement paste

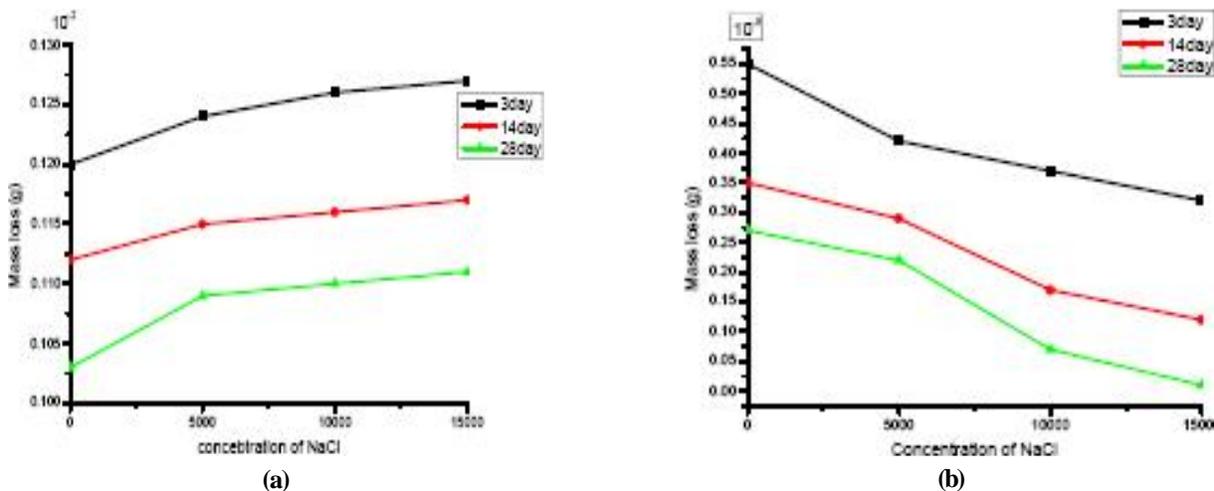


Figure 3 : (a, b) variations of mass loss of the hardened cement pastes with the concentration of NaCl at different curing times, (a) Plain cement paste, (b) Fly ash – Cement paste

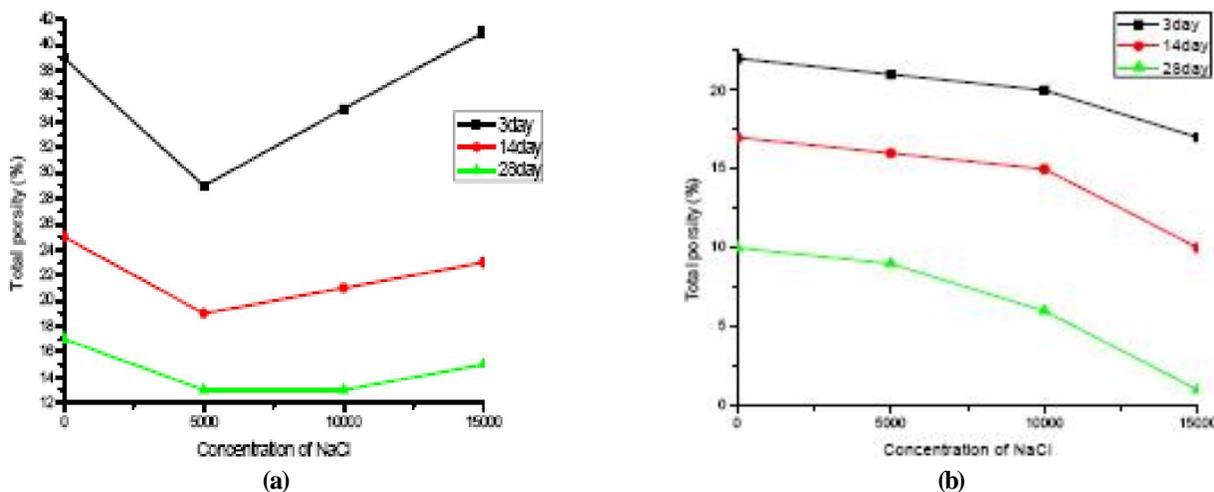


Figure 4 : (a, b) variations of total porosity of the hardened cement pastes with the concentration of NaCl at different curing times, (a) Plain cement paste, (b) Fly ash – Cement paste

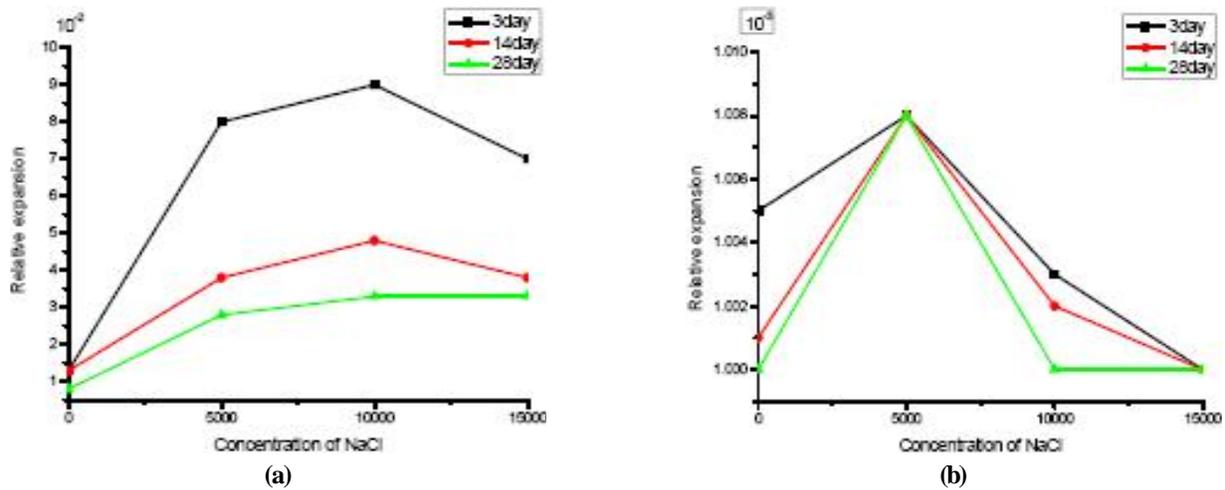


Figure 5 : (a, b) variations of relative expansion of the hardened cement pastes with the concentration of NaCl at different curing times, (a) Plain cement paste, (b) Fly ash – Cement paste

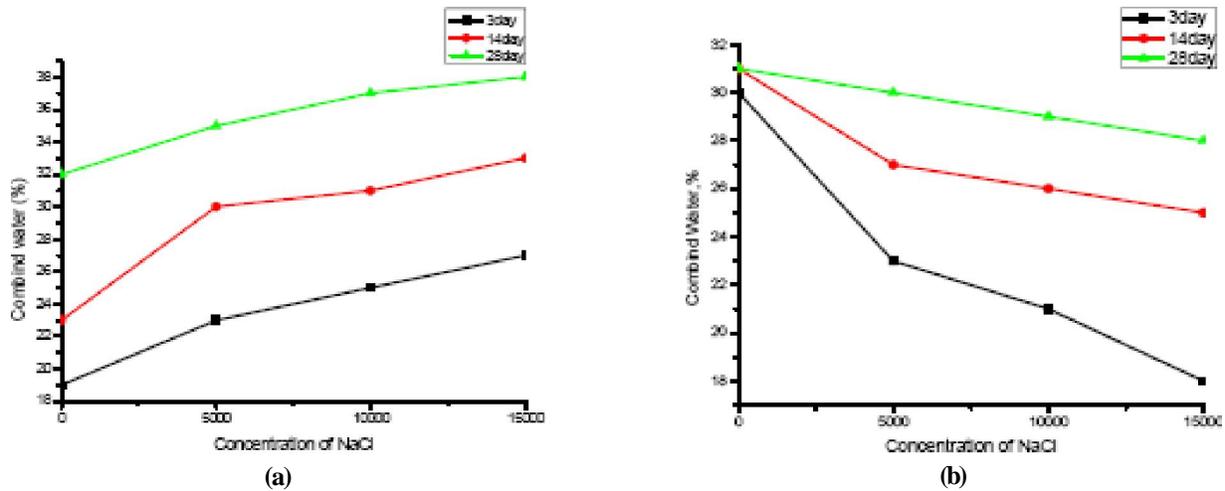


Figure 6 : (a, b) variations of relative expansion of the hardened cement pastes with the concentration of NaCl at different curing times, (a) Plain cement paste, (b) Fly ash – Cement paste

that is leading to increase the combined water inside the structure of samples^[7]. In Figure (6-a) the combined water increasing with increasing the concentration of NaCl due to the acceleration of hydration reactions caused by chloride ions forming additional amounts of calcium silicate hydrates (C-S-H). But in Figure (6-b) it is clear that the combined water content of the blended cement pastes decreases with the NaCl.

CONCLUSIONS

The results are summarized as follows.

1. The physical properties of cement pastes are affected by the exposure to NaCl solutions.
2. The rate of the of mass loss increases with the concentration of NaCl in the samples, the larger amount of mass loss is caused by surface scaling.
3. The use of mineral admixtures (fly ash) increases the ability of cement to withstand aggressive environment and prevent most of the deterioration signs.
4. The porosity of hardened blended cement pastes increases after the concentration 5000 ppm of NaCl due to interaction of chloride with liberated lime from the hydration reaction forming hydrocalumite ($C_3A \cdot CaCl_2 \cdot 10H_2O$) causing softening to the composition with formation of hydration products with a weaker microtexture and a globally more porous cement paste.
5. The interaction of fly ash with the free lime (CH) during the hydration mechanism leading to form additional (C-S-H) phases and consequently decreasing the formation rate of hydrocalumite which soft-

Full Paper

ening the structure of cement pastes.

6. The chemical combined water increases with the curing time, and that is related to the progress of hydration reactions.

REFERENCES

- [1] Hisham M.Khater; *Ceramics-Silikaty*, **54(4)**, 325-333 (2010).
- [2] M.D.A.Thomas, P.B.Bamforth; *Cem.Concr.Res.*, **29(4)**, 487-95 (1999).
- [3] J.Bijen; *Constr.Build.Mater.*, **10(5)**, 309-14 (1996).
- [4] Carl E.Lock; *Mechanism of Corrosion Of Steel in Concrete*, University of Oklahoma, Oklahoma, 73019, USA, (1978).
- [5] G.E.Monfor; J.of the PCA Research and Development Laboratories, **10(21)**, 35 May (1968).
- [6] H.H.Seleem, A.M.Rashad, B.A.El-Sabbagh; *Advances in Science and Technology*, **64**, 19 (2010).
- [7] S.Monosi, M.Colleparidi; *Chemical Attack of Calcium Chloride on The Portland Cement Paste*, *IL Cement* **86**, 97-104 (1989).
- [8] *Standard Test Uethod of Specific Gravity, Absorption and Voids in Hardened*, **04(02)**, 305-306 (1982).
- [9] P.Chindapasirt, C.Jaturapitakkul, T.Sinsiri; *Cem.Concr.Compos.*, **27(4)**, 425-8 (2005).
- [10] H.El-Didamony, M.Y.Haggag, S.A.Abo-El-Enein; *Cem.Concr.Res.*, **8**, 351-358 (1978).