



BioTechnology

An Indian Journal

FULL PAPER

BTIJ, 9(8), 2014 [303-307]

Experiment study on the decomposition properties of snail shell

Yijun Zhang^{1,2*}, Shengyong Liu¹, Huimin Wu²

¹Key Laboratory of Renewable of Henan Agricultural University, No. 63 Nongye Road Zhengzhou City 450002, (CHINA)

²Henan Vocational College of Agriculture, No. 38 Qingnian Road Zhongmou County Zhengzhou City, 451450, (CHINA)

E-mail: zhangjun_003@126.com

ABSTRACT

Snail shell has been calcined on high temperature. Its main components calcium carbonate decomposed into CO₂ and calcium oxide. Calcium oxide is superbase catalyst for the transesterification reaction. By means of differential thermal balance, the decomposition characteristics of snail shell have been studied. And of electron microscope, TEM shows grain morphology characteristics of calcination at different calcining temperature. Organic has decomposed during 257°C-488°C. Decomposition of calcium carbonate starts from 600°C to 800°C, when it was balance. By use of orthogonal analysis, the main influence factors of specific surface area have been optimized. The optimal process parameters are 1050°C calcination temperature, 120µm initial diameter and 1 hour holding time.

© 2014 Trade Science Inc. - INDIA

KEYWORDS

Snail shell;
Specific surface area;
Differential thermal analysis;
Orthogonal design.

INTRODUCTION

In recent years, more and more people preferred to eat snail meat and made it as a fashion that promoted the rapid development of snail farming. Annual production of snail shell over one million tons, mostly of them were discarded as wastes in snail farming area to cause serious pollution of the local water environment. So it is urgent to solve the environmental problems. The main component of snail included more than 95% CaCO₃, a small number of shells hormone (organic matter and trace elements) and a small amount of K, Na, Zn, Sr, Fe, Mg etc. Furthermore, the Snail shell contains no Sulfur^[1]. By firing snail shell, higher degree of alkali reactive solid super base calcium oxide has been obtained, which can be used directly to the catalytic

bio-diesel production. The decomposition product of the snail shell contains a small amount of zinc oxide and strontium oxide which can improve the activity of calcium oxide alkali^[2]. This method not only made the abandoned snail shell into treasure but also played the role of the Environmental Protection. So the preparation of highly active calcium oxide has broad application prospects from snail shell^[3].

The decisive factor of the catalytic activity of solid calcium oxide as super base catalyst is specific surface area. The size of snail shell specific surface area is closely related to the production process, including the particle size of the raw materials, the calcined temperature and the keeping time^[4-6] (up to a certain temperature after the thermostat time). Currently, the research of shell is focused on the desulfurization performance, the

FULL PAPER


microstructure and thermodynamic properties^[7], etc.

In this paper, by means of electron microscopy, the change of CALCINATED surface area can be scanned under the different temperatures. The quality and thermal stability of river snail shells can be learned by differential thermal balance. The optimal production conditions of catalyst can be received by orthogonal experiment method.


MATERIALS AND METHODS

Snails were selected from mountain as the object of study. Firstly, impurities meat on the snail shell surface must be stripped away and be washed with tap water, then sediment and other impurities attached to the surface were removed through steel brush. Secondly, the snail shell soaked for two hours with 0.01% sodium hypochlorite solution then washed it with tap water and steel brush^[8], then soaked for 0.5 hours with 0.6% Hydrochloric acid. At last, the shell has been washed four times with distilled water to remove a variety of organic and inorganic impurities on the surface. In a constant temperature oven for 105°C drying for one hour, crushed sieved 60 mesh, 70 mesh, 90 mesh and 100 mesh were obtained by particle diameter of about 200µm, 160µm, 140µm, 130µm the alternate sample^[9].

Thermal decomposition principle of snail shell is following,



The transient analysis curves of DTA and TG when snail shell decomposed based on differential thermal balance LCT-2B. 20mg different size shell powder was taken as thermal analysis samples. Parameters have been set sampling interval as 1000ms, uniform temperature as 10°C per minute, and the final temperature is set to 1100°C. Because calcium oxide can be poisoned easily by carbon dioxide and water vapor in the air, the reactor should be carried out under the protection of nitrogen. Mechanism of calcium oxide being poisoned is following:



Shell powder treated with alumina crucible in a muffle furnace as 10°C per minute uniform temperature

to 800°C, 950°C, 1000°C or 1100°C (constant calcined temperature). Hitachi S-3400N-a! type scanning electron microscopy was used to observe the morphology of the calcined product of different temperature. Specific surface area of product was measured by low temperature nitrogen adsorption method (BET)^[9]. Absorbed-bate used nitrogen, relative pressure is set to 0.15MPa temperature was set at 180°C (nitrogen liquefaction point is -195°C), thus chemical adsorption can be avoided under low temperature.

Determination of the specific surface area generated by BET (It was discovered by three scientists Brunauer, Emmett and Teller.).

Specific surface area refers to the total surface area per gram of powder, particulate lattice outer surface area and crystal lattice empty cavity surface area superimposed, namely Low-temperature adsorption. The theoretical basis was rules that gas was absorbed in the surface porosity of particles. Under conditions of constant temperature and equilibrium state, the solid surface has a certain amount of adsorption of a certain pressure gas. The gas pressure determines the amount of adsorbed.

This method is currently recognized as the standard method for the measurement of solid surface area. The measurement principle is that physical adsorption would occur in the surface of the material (grain interior and the surface of the external through hole) at low temperatures. The physical adsorption is based on multilayer approach, the first layer is not yet saturated adsorption to produce a second layer on which the adsorption. They may produce a second layer on the third layer adsorption, the adsorption equilibrium stability layers adsorption reached equilibrium at the same time. The measurement of gas adsorption pressure and the adsorption volume can be calculated, and so the specific surface area. Isotherm equation is formula (3):

$$\frac{P/P_0}{V(1-P/P_0)} = \frac{C-1}{V_m C} \times P/P_0 + \frac{1}{V_m C} \quad (3)$$

Where v is Volume of gas adsorption (unit is milliliter), v_m is Monolayer saturation adsorption capacity, P is the adsorption pressure/Pa P_0 is the adsorption saturated vapor pressure/ Pa and C is the

coefficient.

Here let

$$Y = \frac{P/P_0}{V(1-P/P_0)} \quad X = P/P_0$$

$$A = \frac{C-1}{V_m C} \quad A = \frac{C-1}{V_m C}$$

According to the experimental measurements, drawing the curve of $Y=AX+B$.

So the value of V_m was obtained. The surface area can be obtained by formula (4)

$$S_g = \frac{4.36 \times V_m}{W} \quad (4)$$

RESULTS AND ANALYSIS

Decomposition characteristics and morphology of the snail

Figure 1 DAT and TG curves shows the snail shell decomposition process, in the range of 257 °C to 488 °C, accompanied by a strong exothermic peak and with weightlessness weight loss rate of 4.1%, which presumably because of the decomposition of organic matter and release heat. There was one slight weaken exothermic peak in the range of 353°C to 488°C of the calcium carbonate crystal phase transition from

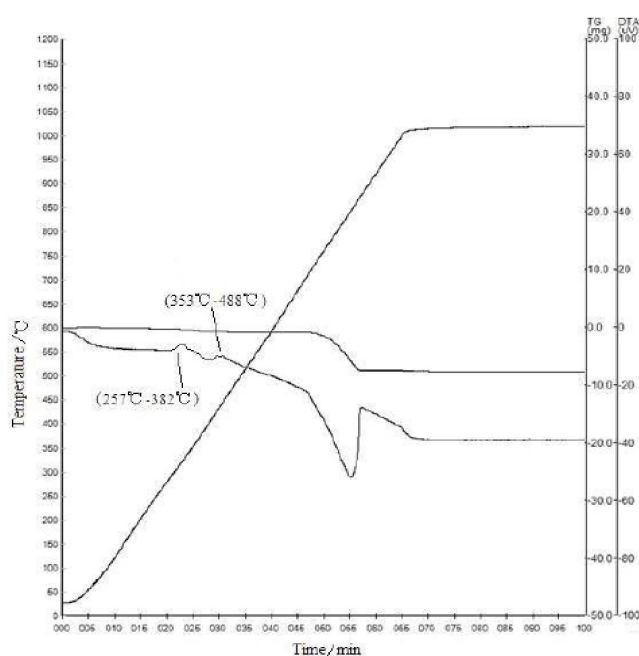


Figure 1 : Thermal analysis spectra of snail shell

aragonite calcite phase caused by the endothermic weakening of the role in the exothermic decomposition of organic matter. Calcium carbonate decomposition occurs when the temperature rose during 600°C to 800°C, and at the same time, rapid weight loss and more endothermic phenomenon accounted that snail shell main ingredients generated Calcium oxide and CO_2 .

As weight loss rate is known that snail shell contains about 94.875% of the calcium carbonate. The sample of decomposition was dissolved with 1% hydrochloric acid and was titrated with 5% sodium carbonate solution, then dried in addition. Calculated production was that snail shell contains about 94.68% of calcium carbonate. When the calcined temperature reached 900°C, TG curve does not change, the decomposition of calcium carbonate reached equilibrium (almost completely decomposition). With continue heating, another period of endothermic generated when lattice defect of calcium oxide gradually reduced. At 1200°C, calcium oxide turned into molten sintering as Figure 2-D as shown. The TEM image shown in Figure 2 for the sample, the product was calcined at different temperatures to 120 mesh particle size snail product particles gradually refined as the temperature increased.

Powder diffractometer was used to verify the composition of the calcined product. Copper was used as the medium. Detecting results were shown in Figure

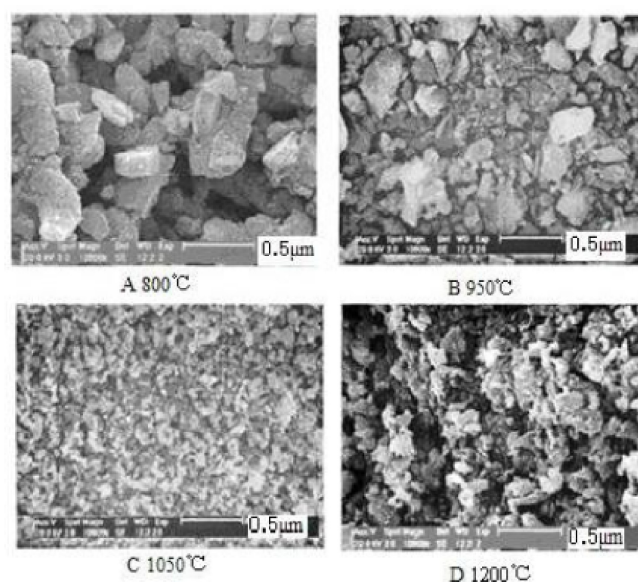


Figure 2 : Scanning electron image of snail shell calcinations at different temperature

FULL PAPER

3. Strong diffraction peak was coincident to that of calcium oxide. It can be seen from the diffraction pattern of the calcined product that calcium carbonate disappeared. Those weak peaks at 100, 102 and 110 represented zinc oxide.

Specific surface area of orthogonal design

The specific surface area of the catalyst particles determines the efficiency of heterogeneous catalytic. Therefore, the orthogonal design method of calcined product was chosen to study the main factors affecting the specific surface area. Pulverized particle diameter A, the calcined temperature B and the holding time C, each with four levels of each factor, and average value thereof. Factors and levels shows as TABLE 1.

TABLE 1 : Factors and levels of specific surface area

levels	Diameter/ μm	temperature/ $^{\circ}\text{C}$	Holding time/h
	A	B	C
1	120	800	0.5
2	150	950	1
3	180	1050	1.5
4	250	1200	2

Accordance with the requirements of the orthogonal design, strict test arranged in a combination of factors, the experimental program and test results are shown in TABLE 2.

As can be seen from the analysis results, the calcined temperature is the most important factor on the contrast surface area, the initial crushing particle size is more and the holding time is important yet. The calcium carbonate decomposes is a reversible reaction, the higher the temperature, the faster and thorough decomposition, so the particle is refined more rapidly. There was certain lattice distortion among the grains of calcium oxide. As the temperature continues to rise, the lattice atoms reconstruction reduced the gap among each other, thereby reducing the specific surface area of the product. So when the temperature was at 1000 $^{\circ}\text{C}$, the product particles reach nanometer level, close to 50nm. Decomposition of the calcium carbonate was from outside to inside, so the smaller the particle the more easily was decomposed and it can easily reach the balance decomposition. Holding time played a certain role on the lattice reconstruction of decomposition

TABLE 2 : Orthogonal analysis of calcined product

No	Factors			Average specific surface area / m^2/g
	A	B	C	
1	1	1	1	32.3
2	1	2	2	43.6
3	1	3	3	53.0
4	1	4	4	37.6
5	2	1	2	28.6
6	2	2	1	39.6
7	2	3	4	38.0
8	2	4	3	30.4
9	3	1	3	31.4
10	3	2	4	44.5
11	3	3	1	38.6
12	3	4	2	41.2
13	4	1	4	32.1
14	4	2	3	34.3
15	4	3	2	34.4
16	4	4	1	28.6
\bar{K}_{1j}	41.6	31.1	35.8	
\bar{K}_{2j}	38.9	37.8	36.8	
\bar{K}_{3j}	34.2	42.8	36.9	
\bar{K}_{4j}	32.6	34.7	36.0	
R_j	8.9	10.6	1.5	

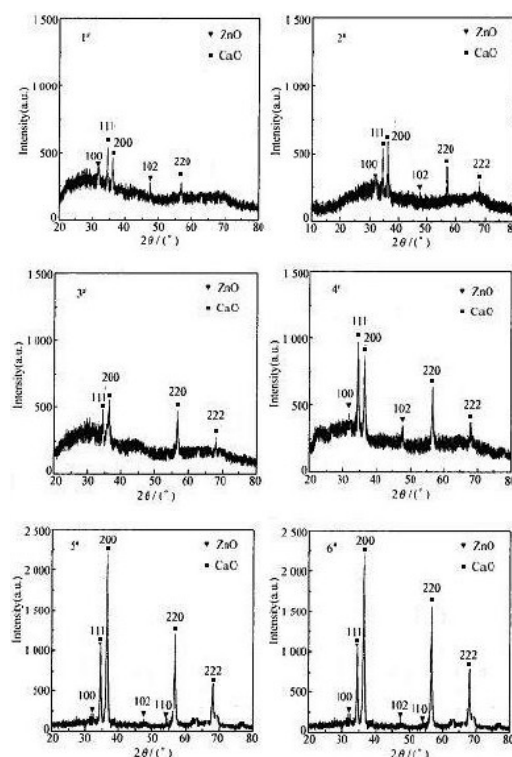


Figure 3 : XRD pattern of calcined product

products, while their impact is relative minor comparing to the calcined temperature.

Figure 3 is a response curve of a orthogonal analysis. Specific surface area reached maximum only when the original particle size was 120 μ m, calcining temperature 1000 °C and holding time was one hour. Therefore, from TABLE 2 and Figure 4, the best process of largest specific surface area was B3A1C2. Calcined snail in accordance with this condition, obtained heterogeneous catalytic 42.53m²/g, and a higher rate of transesterification obtained when it was applied to the production of bio-diesel. So it fully meets the requirements of catalytic superbase catalysts.

CONCLUSION

- (1) The differential thermal analysis of the snail shell discovered its thermal decomposition rule, which two significant changes have occurred in uniform during the heating process. From the DAT and TG curve of snail shell, the decomposition of organic and calcium carbonate have generated with the loss of shell weight. Calcium carbonate content can be calculated about 94.68%. DAT curve becomes less steep when the temperature rose to 800°C, while calcium carbonate is almost completely decomposed.
- (2) TEM image shows that a small amount of snail decomposed when the temperature was at 600°C. As the calcined temperature raised, the calcinations become smaller and smaller. The product gradually molten sintering when the temperature is at 1200°C.
- (3) By orthogonal experimental design, calcined temperature was the most important factors in the three factors. The initial particles followed by holding time certain. Production conditions of the calcined temperature 1050°C, the initial particle size 120 μ m and the holding time one hour were perfect to obtain the optimum surface area of calcinations.

REFERENCES

- [1] B.Pokroy, J.P.Quintana, E.N.Caspi; Anisotropic Lattice Distortions in Biogenic Aragonite. *Nature Materials*. 900-902 (2004).
- [2] K.Takahashi, H.Yamamoto, A.Onoda; Highly Oriented Aragonite Nanocrystal Biopolymer Composites in an Aragonite Brick of the Nacreous Layer of Pinctada Fucata. *Chemical Communications*, **8**, 996-997 (2004).
- [3] Vicente Gemma, Martinez Mercedes, Aracil Jose; Integrated bio-diesel production, A comparison of different homogeneous catalysts systems. *Bioresource Technology*, **92**, 297-305 (2004).
- [4] Nobutake Nakatani, Hitoshi Takamori, Kazuhiko Takeda, Hiroshi Sakugawa; Transesterification of soybean oil using combusted oyster shell waste as a catalyst. *Bioresource Technology*, **100**, 1510-1513 (2009).
- [5] Bai Hai-xin, Shen Xiao-zhen; Synthesis of porous CaO microsphere and its application in catalyzing transesterification reaction for bio-diesel. *Transactions of Nonferrous Metals Society of China*, **19**, 672-677 (2009).
- [6] H.Hattori; Solid base catalysts: generation of basic sites and application to organic synthesis. *Appl.Catal A:General*, **222**, 247-259 (2001).
- [7] M.D.Serio, R.Tesser, L.Lu Pengmei, E.Santacesaria; Heterogeneous catalysts for biodiesel production. *Energy Fuel*, **22**, 207,217 (2008).
- [8] L.T.Kuhrr spearing, H.Kessler, E.Chateau, et. al.; Fracture mechanisms of the strom bus gigas conch shell; implications for the design of brittle laminates. *Scil*, **31**, 65-83 (1996).
- [9] Y.Zhang, X.Shen, et. al.; Calcination of waste snail shell used as catalyst in producing biodiesel. in *Proceedings of the Conference on 2011 International Conference on Energy, Environment and Sustainable Development ICEESD*, Shanghai, October 21-23, China, 44-47 (2011).