



Trade Science Inc.

December 2007

Volume 3 Issue 4

Macromolecules

An Indian Journal

Full Paper

MMAIJ, 3(4), 2007 [150-152]

Orientation of carbazole molecule in the mixed Langmuir-Blodgett films

S.Biswas^{1,2}, D.Bhattacharjee¹, S.A.Hussain^{1*}

¹Department of Physics, Tripura University Suryamaninagar-799130, Tripura, (INDIA)

²Department of Chemistry, Tripura University, Suryamaninagar-799130, Tripura, (INDIA)

Phone: +91 381 2375317; Fax: +91 381 2374801

E-mail: tuphysic@sancharnet.in, sa_h153@hotmail.com

Received: 20th September, 2007 ; Accepted: 25th September, 2007

ABSTRACT

This paper reports the molecular orientation of carbazole(CA) molecules in the mixed Langmuir-Blodgett(LB) films of carbazole in stearic acid(SA) matrix. Changes in the intensities of the absorption bands are observed by rotating the LB films, keeping the direction of the incident radiation unchanged. Maximum intensities of the absorption bands are observed when the LB films are kept at an angle of 45°C with the incident radiation. For other angles of orientations; intensities of the absorption bands are minimum. This certainly confirms the fact that CA molecules have preferred orientation on the substrate of the LB films.

© 2007 Trade Science Inc. - INDIA

KEYWORDS

Carbazole;
Nonamphiphilic;
Langmuir-Blodgett films;
UV-Vis absorption
spectroscopy.

INTRODUCTION

The Langmuir-Blodgett(LB) technique offers a unique method to fabricate ultrathin organized assembly of molecules^[1] where the optical and electrical properties may be manipulated with ease. Owing to this, the LB technique is unique and versatile in fabricating various optoelectronic and molecular electronic devices^[2-5].

Carbazole(CA) and its derivative have found extensive technological applications in organic photoconductors^[2] and electroluminescent devices^[3-5]. They have their unique photophysical characteristics such as intense and well characterized absorption and fluorescence spectra^[6-7]. Owing to their excellent optical and electronic properties, various derivatives of carbazole were synthesized and studied in the Langmuir-Blodgett films^[6-12].

However the orientation of this molecule in LB films

was not studied before. This paper reports a unique observation of orientation of carbazole(CA) molecules in the mixed LB films of CA doped in stearic acid(SA) matrix, using UV-Vis absorption spectroscopy. It was observed that the intensity of the absorption bands in the LB films depend on the angle in which the quartz slides was placed. Interestingly it was observed that, the intensity of absorption bands become maximum when the LB films were kept at an angle of 45°C with the incident radiation.

EXPERIMENTAL

CA was purchased from Aldrich Chemical Company, USA and vacuum sublimed followed by repeated recrystallization before use. SA(purity 99%) from sigma, USA, was used as received. The solvent chloroform (SRL, India) was of spectral grade and its fluorescence

spectra were checked before use. Langmuir-Blodgett film deposition instrument (Apex, 2000C, India) was used for the study of monolayer characteristics and also for multilayer film deposition. The subphase used was triple distilled deionised water having pH 6.5 in equilibrium with atmospheric carbon dioxide. The solution of CA, SA as well as CA-SA mixtures are prepared in chloroform solvent and were spread on the subphase with the help of micro syringe. Surface pressure was recorded by Wilhelmy plate arrangement described elsewhere^[13]. All the films are 10 bilayered. Fluorescence grade quartz slides were used for film deposition and deposition was carried out at a surface pressure of 15mN/m.

UV-Vis absorption spectra of these films were measured by a Perkin-Elmer Lambda 25 spectrophotometer. All the measurements were performed at room temperature(25°C).

RESULTS AND DISCUSSION

UV-Vis absorption spectroscopic study

Figure 1 shows the UV-Vis absorption spectra of mixed LB films of CA(0.5M) in SA matrix placed at angles 0°C, 15°C, 30°C, 45°C, 60°C and 75°C with the incident radiation alongwith the respective solution and microcrystal spectrum.

Absorption spectrum of CA in chloroform solution shows distinct bands within 225-350nm region with intense and sharp high energy bands having peaks at 247 and 292nm alongwith a weak hump at around 258nm, owing due to S_2-S_1 transition which is directed parallel to the long axis of the molecule. There are two other low intense but prominent vibrational bands in the 300-350nm regions, with maxima at around 319nm and 331nm corresponding to S_1-S_0 transition which is directed parallel to the short axis of the molecule.

The CA microcrystal spectrum also shows almost identical vibrational band system except an increase in intensity. However, the high energy bands in the microcrystal spectrum become broadened and blue shifted. In addition, the band with peak at 292nm in CA solution spectrum is totally absent in the corresponding microcrystal spectrum.

The absorption spectra of the mixed LB films of

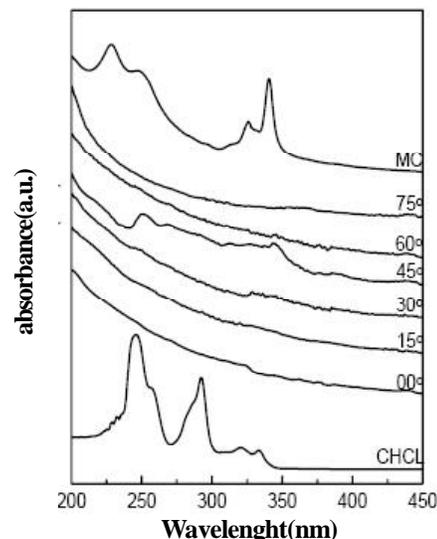


Figure 1: UV-Vis absorption spectra of mixed LB films of CA(0.5M) in SA matrix placed at angles 0°C, 15°C, 30°C, 45°C, 60°C and 75°C with the incident radiation alongwith the CA solution and microcrystal spectrum

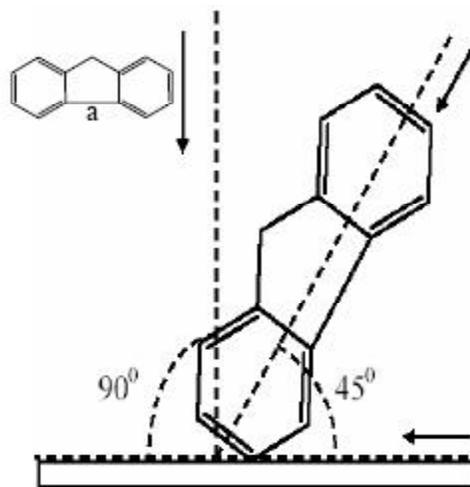


Figure 2: Schematic representation of the alignment of the carbazole(CA) molecule on the substrate of the LB films. Inset shows the molecular structure of CA(a)

CA in SA matrix, kept at various angles with the incident radiation are also shown in figure 1. Interestingly it was observed that when the mixed LB films were kept at an angle of 45°C with the incident radiation prominent vibrational bands are observed both at the high energy and low energy region. These bands are remarkably similar with the microcrystal bands. However, for other angles, namely, 0°C, 15°C, 30°C, 60°C, 75°C, which the films make with the incident radiation, no absorption bands are observed.

Full Paper

The appearance of absorption bands at a particular angle of orientation of the films with the incident radiation definitely concludes the fact that carbazole molecules have a specific orientation in the LB films.

A schematic representation of the alignment of the carbazole(CA) molecules on the substrate of the LB films is shown in figure 2.

A plausible explanation is that at 45° angle of orientation of the LB films with the incident radiation, the electric field of the incident radiation is along the direction of the dipole moment of the CA molecules. Hence maximum absorption of incident radiation occurred. For other angle of orientation direction of the electric field of the incident radiation does not coincide with the direction of the dipole moment of the CA molecules.

CONCLUSION

In conclusion, our results show that carbazole molecules have specific orientation in the mixed LB films. The angle dependence absorption studies of the mixed LB films indicate that when the mixed LB films are kept at an angle of 45° with the incident radiation, prominent absorption bands are observed.

ACKNOWLEDGMENT

The authors are grateful to DST and UGC Govt. of India for providing financial assistance through FIST-DST Project No. SR/FST/PSI-038/2002 and UGC minor research project No. Ref No. F.1-1/2000(FD-III)/399 and Sanction Ref. No.F. 31-30/2005 (SR).

REFERENCES

- [1] A.Ulman; 'An introduction to Ultrathin Organic Films: From Langmuir-Blodgett Films to Self Assemblies', Academic Press, New York, (1991).
- [2] N.Kim, E.W.Stephen; *Macromolecules*, **18**, 741 (1985).
- [3] A.Aoki, Y.Tamagawa, T.Miyashita; *Macromolecules*, **35**, 3686 (2002).
- [4] K.K.Justin Thomas, J.T.Lin, Y.T.Tao, C.H.Chuen; *Chem.Mater.*, **16**, 5437 (2004).
- [5] F.Sanda, T.Nakai, N.Kobayashi, T.Masuda; *Macromolecules*, **37**, (2004).
- [6] Krishanu Ray, T.N.Misra; *Langmuir*, **13**, 6731 (1997).
- [7] A.K.Dutta; *Langmuir*, **12**, 5909 (1996).
- [8] Y.Liu, M.Liu; *Thin Solid Films*, **415**, 248 (2002).
- [9] Jiu-Yan Li, Ming-Li Peng, Li-Ping Zhang, Li-Zhu Wu, Bo-Jie Wang, Chen-Ho Tung; *J.Photochemistry and Photobiology A*, **150**, 101 (2002).
- [10] S.A.Hussain, P.K.Paul, D.Bhattacharjee; *J.Colloid and Interface Science*, **299**, 785 (2006).
- [11] T.Nagamura, K.Toyozawa, S.Kamata T.Ogawa; *Thin Solid Films*, **210**, 332 (1992).
- [12] N.Ohta, S.Okazaki, S.Y.I.Yamazaki; *Thin Solid Films*, **258**, 305 (1995).
- [13] S.Deb, S.Biswas, S.A.Hussain, D.Bhattacharjee; *Chem.Phys.Lett.*, **405**, 323 (2005).