



Trade Science Inc.

Materials Science

An Indian Journal

Full Paper

MSAIJ, 2(6), 2006 [274-282]

Thermal Behaviour Of Two Tunisians Kaolins Structural Changes And Textures Results

*Corresponding Author*

M.Chelly
Unite Materiaux, Technopole Borj Cedria,
B.P. 95-2050 Hammam-Lif, (TUNISIA)
Email:mohamed_sagittaire@yahoo.fr

Received: 29th November, 2006

Accepted: 14th December, 2006

Web Publication Date : 27th December, 2006

*Co-Author*

E.Srasra
Unite Materiaux, Technopole Borj Cedria, B.P. 95-2050
Hammam-Lif, (TUNISIA)

ABSTRACT

The purpose of this work is to characterise and study the thermal behaviour of two Tunisians kaolins. Two samples are selected for this study. The samples are tested by chemical analysis (CA), X-ray diffraction (XRD), differential thermal analysis (DTA), infrared spectroscopy (IR), cation exchange capacities (CEC) and specific areas (BET) in order to determine their chemical and mineralogical composition and structural differences. The evolution of specific surface according to the temperature of the Kasserine samples after thermal treatment shows an abrupt diminution at 700°C that are interpreted by a process of sintering. The thermal treatment of the two clays at 1200°C, shows the apparition of a new phase that is the mullite. This mullite is identical to mullite gotten by the process sol-gel from the synthesis of the pure aluminosiloxane.

© 2006 Trade Science Inc. - INDIA

KEYWORDS

Kaolin;
Thermal transformation;
Specific surface.

INTRODUCTION

Ceramic product depends on the nature and the properties of utilized raw material. The increase in temperature for singly fired ceramic clays exceed the energy threshold of the reactivity of mineral material and produces a series of reaction and transformations that lead to the formation of new phases

and the disappearance of others^[1]. For the some firing conditions the halloysite clay produced a higher bulk density than the kaolinite clay as well as finer mullite crystals. Mullite is formed in kaolinite clay at a lower temperature than in halloysite clay^[2]. The kaolinite forms metakaolinite by heating from 550°C to 950°C, and mullite mainly forms above 1200°C^[3].

The objective of this paper is to study the thermal

transformation of two Tunisians kaolins chooses.

MATERIALS AND METHODS

Two samples are selected for this study: Kasserine clay (K) and Tabarka clay (T). We add a suffix "b" or "p" to indicate respectively if the clay is crude or purified.

Purification

The clay fraction was purified by classical methods^[4], repeated cation exchange with 1N NaCl solution, washing and sedimentation and dialysis. The fine clean sediment was freeze dried.

Chemical analysis

The samples are attacked by a mixture of three acids (HCl, H₂SO₄ and HNO₃); all elements pass in solution only the silica that it measured out by gravimetric^[5].

The chemical elements, as Al, Fe, Mg, Ca, Na and K are measured by atomic absorption.

X-ray diffraction

Mineralogical analysis was performed by XRD, using a Philips diffractometer PW 1050/81, with the $K\alpha_{1,2}$ radiation of the copper. In this method, oriented specimens are prepared on glass microscope slides. The slides have a density of 20 mg of samples and were successively given treatment of:

- i) Drying at 20°C
- ii) Heating for two hours an 500°C

Infrared spectroscopy

FT-IR spectra were recorded in the region 4000-350 cm⁻¹ in an EQUINOX model 55 infrared Fourier transform spectrometer, using the KBr pellet technique (about 2 mg of sample and 200 mg of KBr were used in the preparation of the pellets).

Cation exchange capacity

Clay is saturated first with other solutions. The excess of the reagent added is measured by volumetric method.

N₂ adsorption experiments

The specific surface areas of the samples were determined by the corresponding nitrogen adsorption

isotherms at 77 K, obtained from Micrometric Autosorb 2050 Analyser, after out degassing the samples at 120°C, with the residual pressure of 10-5 mmHg. The BET method was used for the corresponding calculations. Total pore volume (Vt) was determined at P/P0=0.98.

RESULTS AND DISCUSSION

Characterization of the two clays

The centesimal compositions of raw and purified samples are given in TABLE 1. The following preliminary points may be noticed:

- a) The loss on ignition of the Kasserine clay is very important (33.20 %); it can be due to the presence of a supplementary water layer.
- b) The (SiO₂/Al₂O₃) ratio is close to 1 for all samples. Therefore we can deduct that the two minerals are of types 1/1.
- c) The (SiO₂/Al₂O₃) ratio of the Tabarka clay (1.15) is very close to the theoretical kaolinite 1.18^[6].
- d) The amounts of SiO₂ (38.77 %) and Al₂O₃ (37.20 %) of purified Tabarka clay are nearly equal to those given by the literature for a kaolinite.

TABLE 1: Chemical analysis of the samples

	SiO ₂	Al ₂ O ₃	Fe ₂ O ₃	CaO	MgO	K ₂ O	Na ₂ O	ZnO	PF
K _b	35,12	28,90	0,19	0,63	0,28	1,29	0,15	0,24	33,20
K _p	45,95	28,52	0,17	0,08	0,12	0,08	0,14	0,25	24,69
T _b	44,36	38,77	0,50	0,33	0,08	0,11	0,02	0,17	15,66
T _p	46,03	37,20	0,46	0,36	0,08	0,05	0,04	0,19	15,59

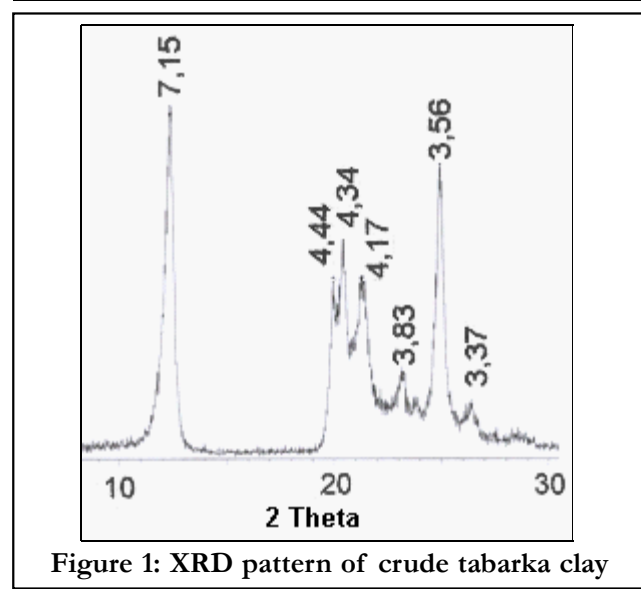


Figure 1: XRD pattern of crude tabarka clay

Full Paper

The XRD pattern of the Tabarka clay (figure 1) shows sharp peaks at $d = 7.15, 4.45, 4.35, 4.17, 3.84$ and 3.57 \AA due to well crystallized kaolinite^[7].

The XRD pattern of the Kasserine clay (figure 2) shows sharp peaks at $d = 10, 4.48, 3.34$ and 2.58 \AA due to halloysite $4H_2O$ ^[8].

The diffractograms (figure 3) show that these two samples are respectively of kaolinite and halloysite that will be destroyed at 500°C . The confirmation

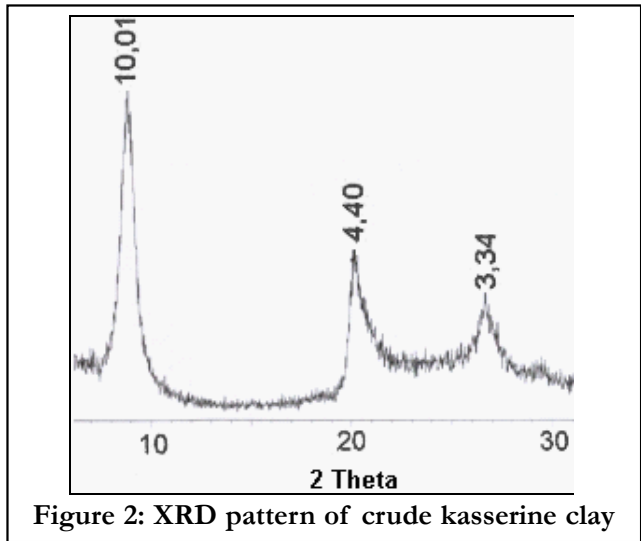


Figure 2: XRD pattern of crude kasserine clay

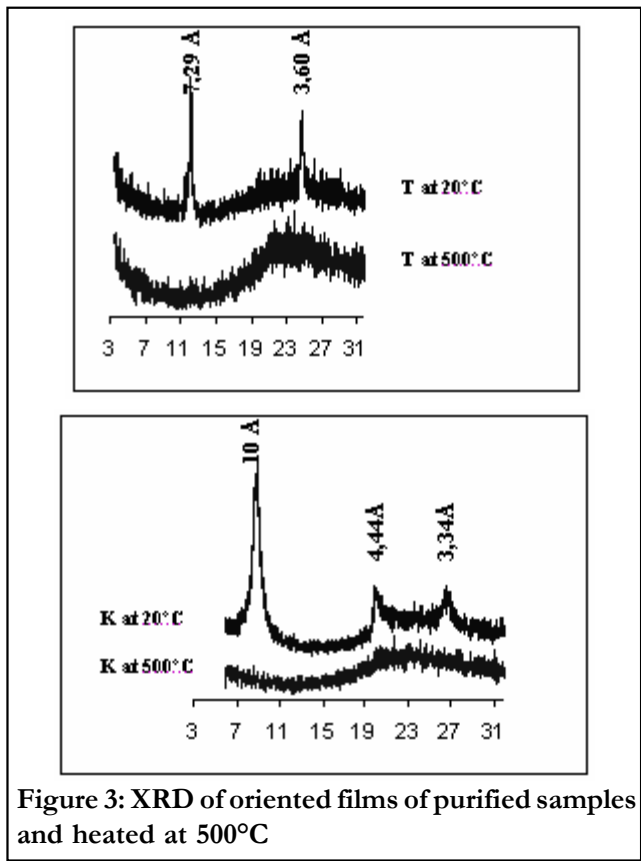


Figure 3: XRD of oriented films of purified samples and heated at 500°C

TABLE 2: Identification of samples

Minerals	Normal Glass	Glass heated at 500°C
Kaolinite	$7,29 \text{ \AA}$	Detruite
Halloysite	10 \AA	Detruite

of our results with those gotten by other authors^[9] is returned in the TABLE 2.

The exam of IR spectra shows that (figure 4, 5):

- a) IR spectra of raw and purified samples are identical; so no foulness associated to the two clays.
- b) In the region between 3500 and 4000 cm^{-1} , the

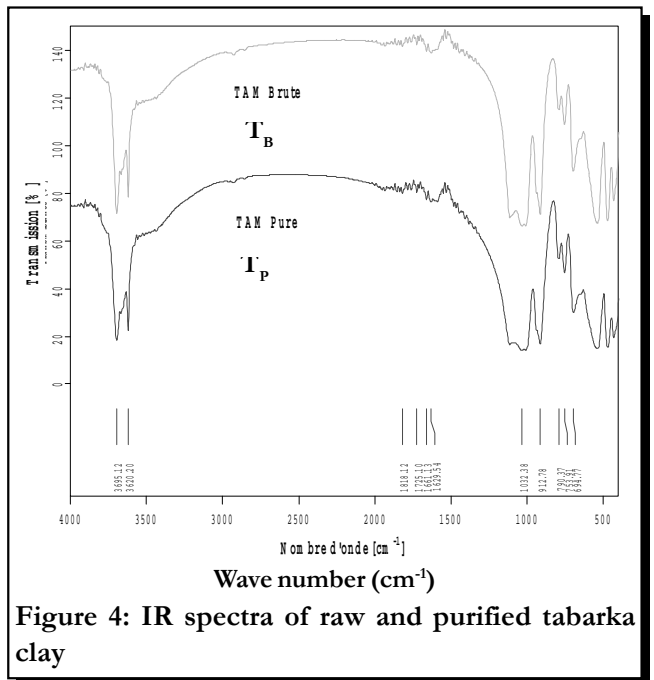


Figure 4: IR spectra of raw and purified tabarka clay

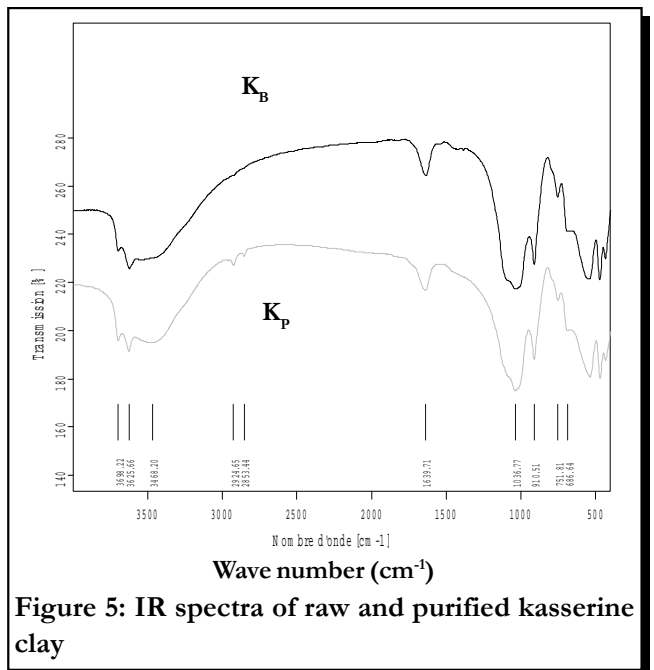


Figure 5: IR spectra of raw and purified kasserine clay

TABLE 3: IR bands (cm⁻¹) of tabarka clay

3695, 3660 and 3620	Al-OH of valence
940 and 913	Al-OH of deformation
1032	Si-O-Si of valence
1005	Si-O-Al of valence
695 and 539	Si-O-Al of deformation


IR spectrum of the tabarka clay (figure 4) shows thins and intense bands whereas the bands of the kasserine clay (figure 5) are larges and less intense. It proves that tabarka clay is better crystallized than Kasserine clay.

- c) Referring on results of IR spectroscopic analysis for a kaolinite, given by Vander Marel and Bentels Pacher in 1976, we deduce that Tabarka clay is a kaolinite well-crystallized (TABLE 3).

Figure 5 shows bands at 3698, 3625 1036 and 912 cm⁻¹ characterizes the clayey mineral of kaolin family^[10]. The adsorption massif at 3468 cm⁻¹ and the band of deformation at 1640 cm⁻¹ (vibrations OH of the hydration water clay), show that the kasserine clay is a halloysite.

Figure 6 presents the DTA curves of the studied samples. The main changes pointed out by TG and DTA, during the heating of the samples are the following:

- a) Lower to 200°C: a first endothermic pick that can be correlated with a pre-dehydration process, which takes place as a results of the reorganization in the octahedral layer, first occurring at the OH of the surface^[11]. This explains the importance of the first loss of the Kasserine sample (TABLE 4) in relation to the one of the Tabarka sample.
- b) 500-600°C: a second endothermic pick due to dehydroxylation of the clay. During this temperature kaolinite forms metakaolinite by dehydroxylation^[12].
- c) 976-1000°C: an exothermic pick that doesn't correspond to a weight loss but it indicates the transition of phase to high temperature of the amorphous product, due to the decomposition of the kaolinite. In well-crystallized samples the decomposition of kaolinite starts at higher temperature^[13]. So the observation of these two picks of our samples permits us to conclude that

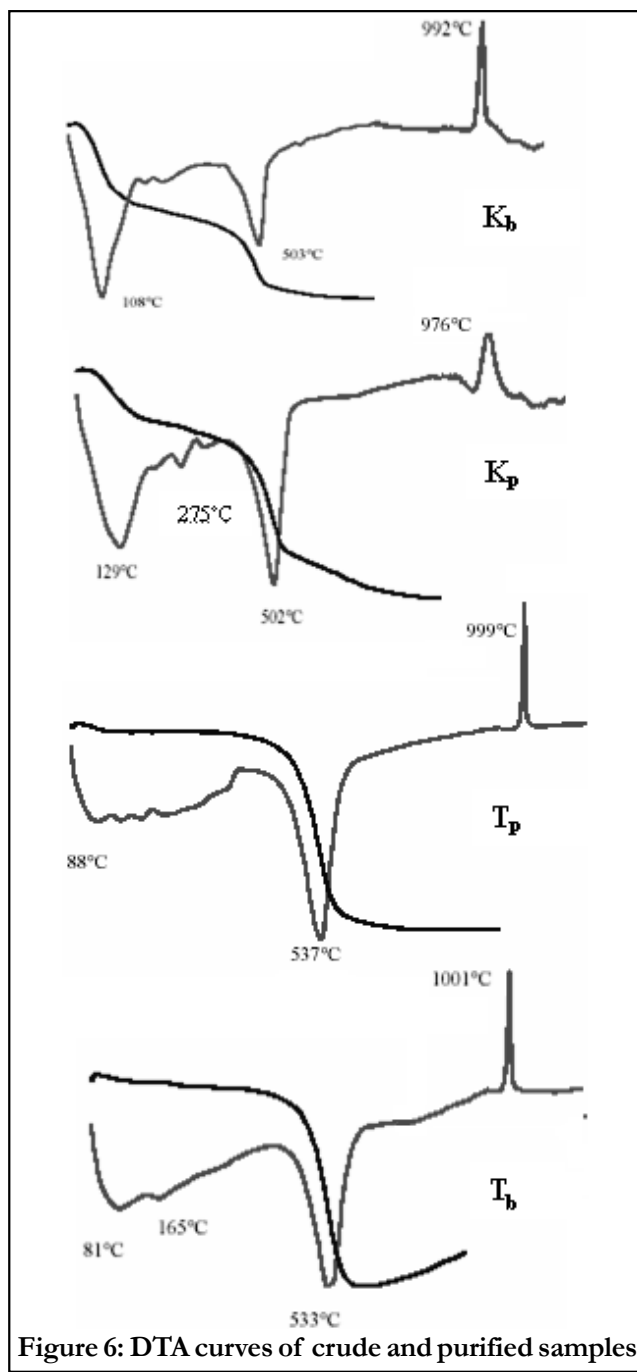**Figure 6: DTA curves of crude and purified samples****TABLE 4: Losses in mass of samples**

Samples	1 st loss (%) T < 200°C	2 ^{sd} loss (%) 400 < T < 600°C
K _b	3,89	5,04
K _p	1,44	6,62
T _b	0,50	12,77
T _p	1,32	13,78
Weight losses (Ross and Kerr, 1931)		
Kaolinite	1 – 2 %	13 %
Halloysite	2 – 4 %	6 – 14 %

Full Paper

Tabarka sample is better crystallized than Kasserine sample.

- d) The calculation of losses in mass (TABLE 4) of kasserine clay and Tabarka clay shows that it is respectively a halloysite and a kaolinite^[14]

Figure 7 presents the isotherms of adsorption-desorption of Kasserine clay and Tabarka clay.

The raw sample of kasserine has an important power of adsorption compared to the purified sample.

The adsorption-desorption isotherms of Tabarka clay are confounded. This clay is not porous characteristic of kaolinite. Whereas the isotherms of desorption of the Kasserine clay present hysteretic buckles what indicates that this clay is porous.

The Kasserine clay presents the best power of adsorption of the two clays.

Specific surface values, determined from the isotherms of adsorption, of the two samples are represented in the TABLE 5.

The specific surface is not sufficient for the characterization of clayey mineral. The specific surface of kaolinite is lower to 25 m²/g^[15]. In our case the specific surface value of tabarka clay (TABLE 5) its

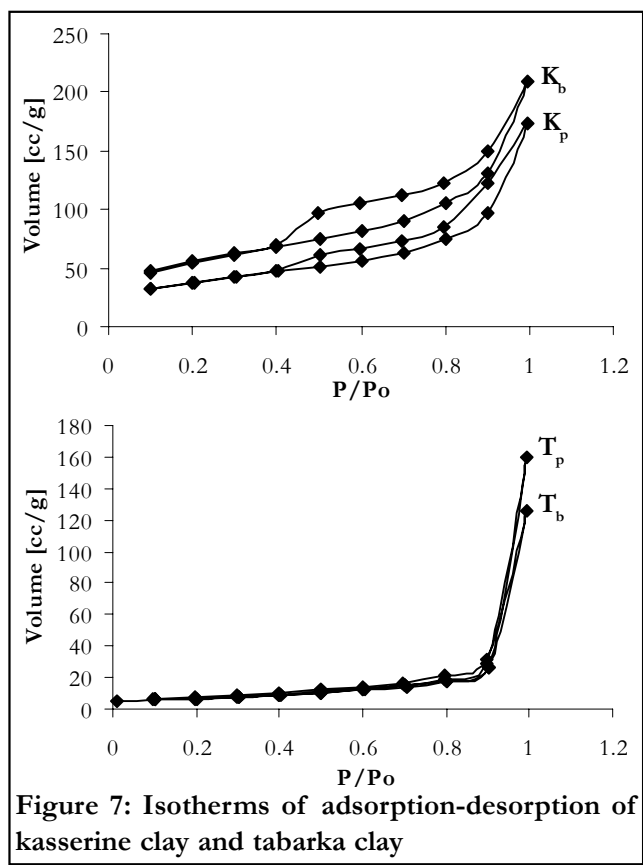


Figure 7: Isotherms of adsorption-desorption of kasserine clay and tabarka clay

TABLE 5: Specific surface of samples

Samples	Specific surface (m ² /g)
K _b	233,96
k _p	128,27
T _b	24,57
T _p	24,60

TABLE 6: C.E.C of samples

Samples	C.E.C (meq/100g of heated clay)
K _b	40,11
K _p	39,84
T _b	3,15
T _p	3,15
C.E.C of some clayey minerals (Kelley, 1948)	
Kaolinite	3 - 15
Halloysite 2H ₂ O	5 - 10
Halloysite 4H ₂ O	40 - 50

24.5 m²/g corresponds to kaolinite.

The values of C.E.C of the raw and purified clays are nearly identical (TABLE 6), what confirm that these two samples don't contain any foulness.

According to the literature values^[16] of the C.E.C we noted that:

- The C.E.C of the Kasserine sample (40.11 meq/100g of clay charred), corresponds to Halloysite 4H₂O.
- The value of the C.E.C of the Tabarka sample (3.15meq/100gs of heated clay), corresponds to kaolinite.

Study of the thermal behaviour of the kaolinite of tabarka and the halloysite of kasserine

The thermal analysis is realized by heating samples to different temperatures (100, 300, 500, 700, 1000 and 1200°C), during one hour. The heated samples are analyzed by different techniques (XRD, IR and specific surface analysis).

1. Study of the thermal behavior by XRD

Figures 8, 9 present respectively the XRD patterns to different temperatures of the Tabarka and Kasserine samples.

The XRD patterns at 100°C (Figure 9), shows a sharp peaks at $d = 7.41, 4.41$ and 3.59 \AA characteristic of kaolinite, what explains the departure of water molecules of the halloysite. The kaolinite is de-

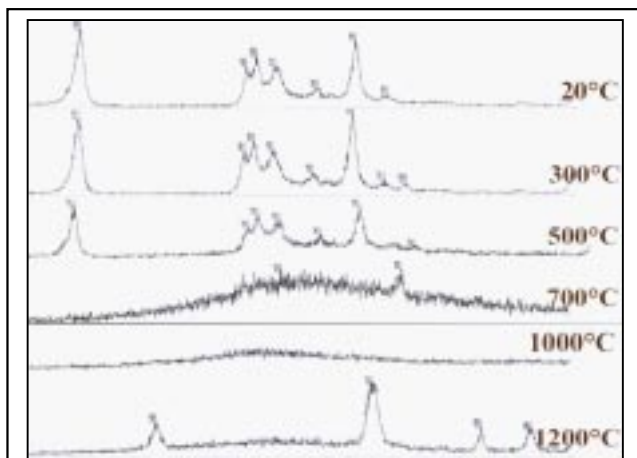


Figure 8: XRD patterns of tabarka samples to different temperatures

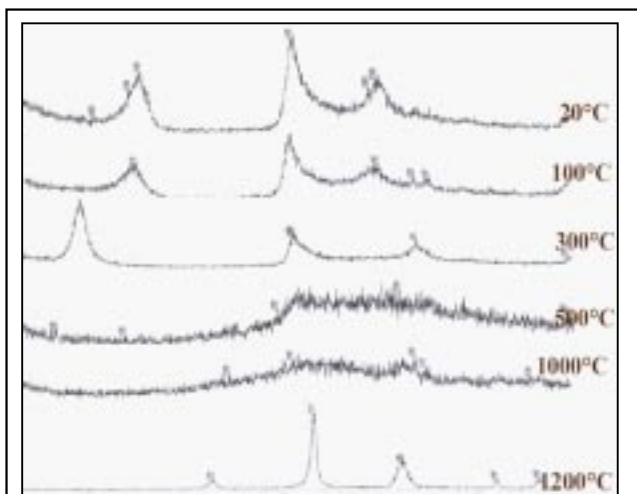


Figure 9: XRD patterns of kasserine samples to different temperatures

stroyed to 550°C due to the formation of an amorphous dehydration product identified as metakaolinite after an endothermic reaction. At 1000°C, the structure of the two samples is completely changed what interpreted by the formation of crystalline product from the next amorphous intermediate phase results in a prominent exothermic reaction at 980°C^[17]. The two diffractograms obtained at 1200°C, show a sharp peaks at $d=5.41, 3.41, 2.89$ and 2.70 \AA relatives to a new phase that is the mullite.

The diffractogram of Tunisian mullite (Figure 10) gotten by thermal treatment of the Tabarka clay is simulated to XRD pattern of a pure mullite (Figure 11) but picks are less resolute that can be due to a bad crystallization.

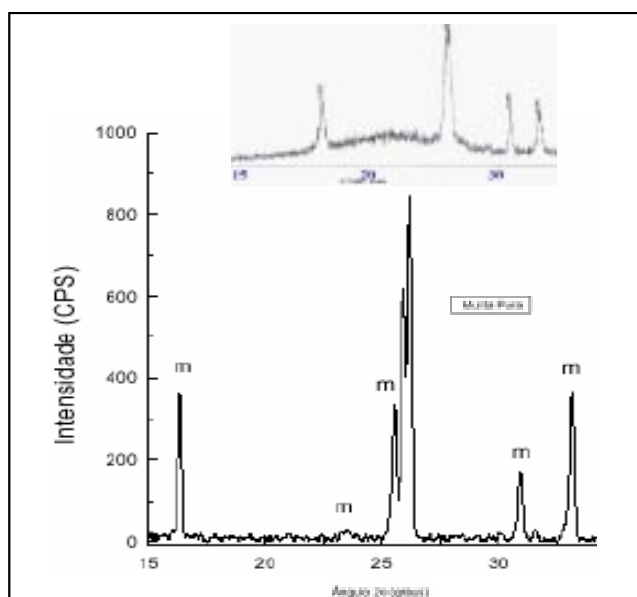


Figure 10: XRD pattern of tabarka clay heated at 1200°C and the diffractogram of pure mullite (M.F. de Souza and J.Yamamoto, 1999)^[18]

2. Study of the thermal behavior by IR

Figure 11 and 12 present respectively the IR spectra of Kasserine and Tabarka samples, obtained after thermal treatment. After the thermal treatment of samples, the transformation of kaolinite to metakaolinite is confirmed by the absence of detectable Al-O-H bands at 913 cm^{-1} . The reduction of 539 and 913 cm^{-1} and the appearance of a new band at 786 cm^{-1} can be connected with the change from octahedral coordination of Al^{3+} in kaolinite to tetrahedral coordination in metakaolinite^[19]. The characteristic bands of kaolinite have been disappeared after the thermal treatment over 500°C. a new band at $2850\text{-}3500 \text{ cm}^{-1}$ is observed in the sample treated at 700°C and is reduced as the treatment temperature is increased.

The specters of the two clay samples, heated to 1200°C, show the apparition of a new phase are similar to the mullite spectera (Figure 13) observed using FTIR. This mullite is prepared from sol-gel process by the synthesis of the pure aluminosiloxane^[20].

3. Study of the thermal behavior by specific surface

Figure 14 presents the adsorption-desorption isotherms of kasserine samples after thermal treatment, show a progressive diminution of the porosity until

Full Paper

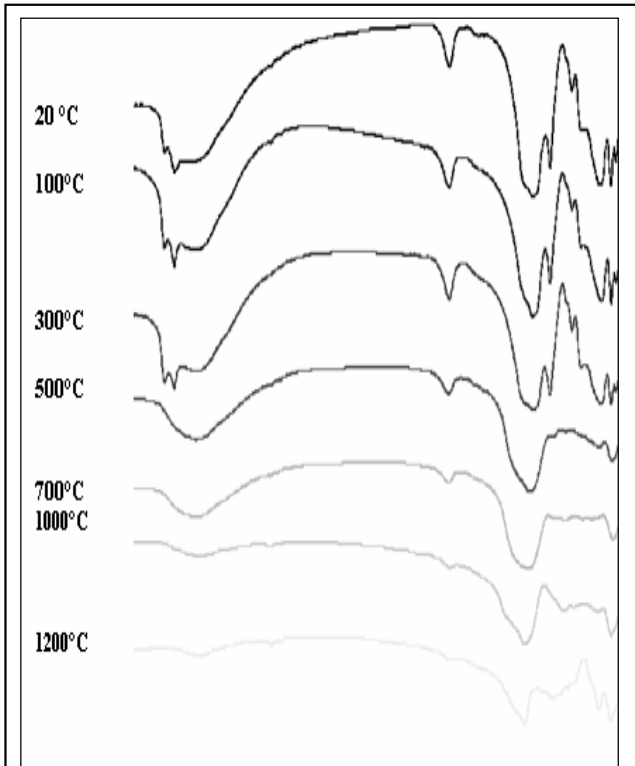


Figure 11: IR of kasserine samples after thermal treatment

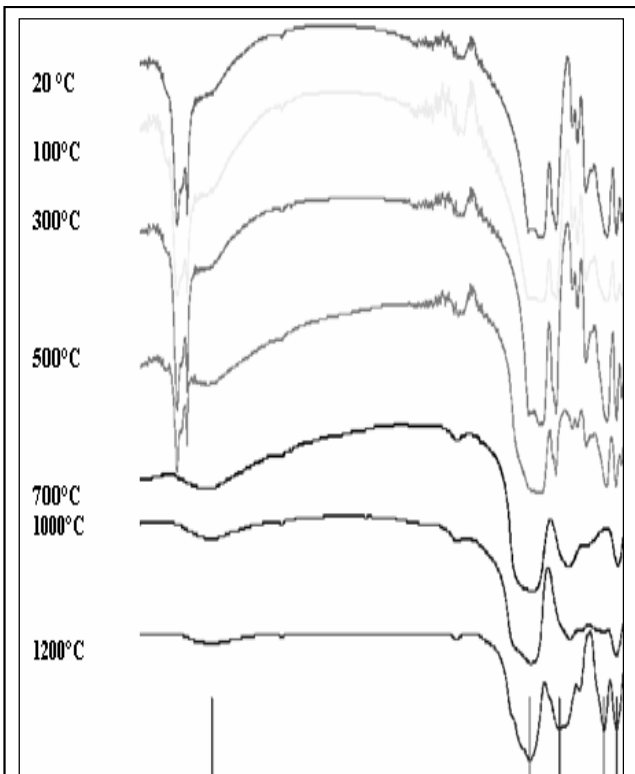


Figure 12: IR of tabarka samples after thermal treatment

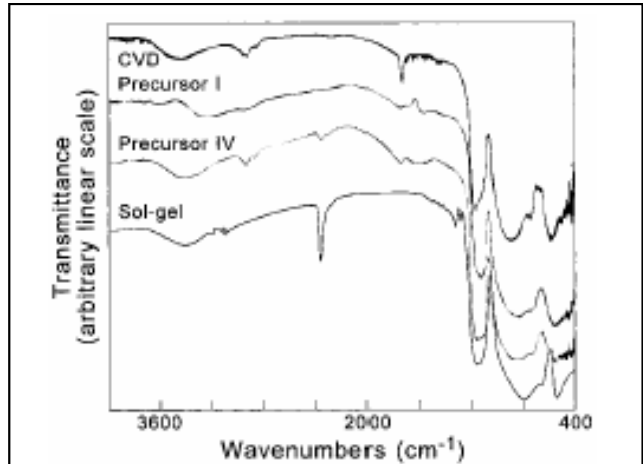


Figure 13: Chemical homogeneity in mullite prepared from polymeric precursors can be observed using FTIR^[20]

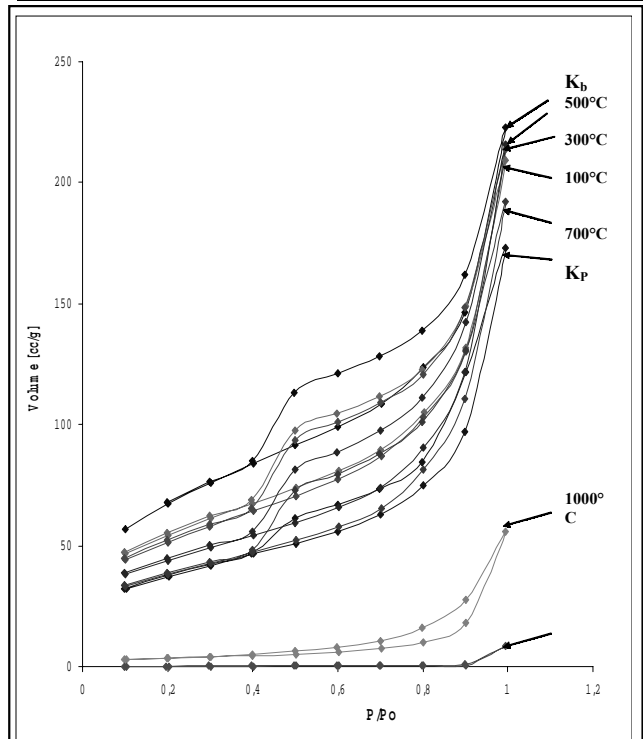


Figure 14: Adsorption-desorption isotherms of kasserine samples after thermal treatment

completely disappears at 1200°C.

The specific surfaces of two clays obtained after thermal treatment are represented in the TABLE 7

The specific surface of Kasserine clay (233.96 m²/g to 20°C) remains very important until the temperature of 700°C, what reveals some catalytic applications to high temperature.

The specific surface of tabarka clay according to the temperature (Figure 16) remains constant un-

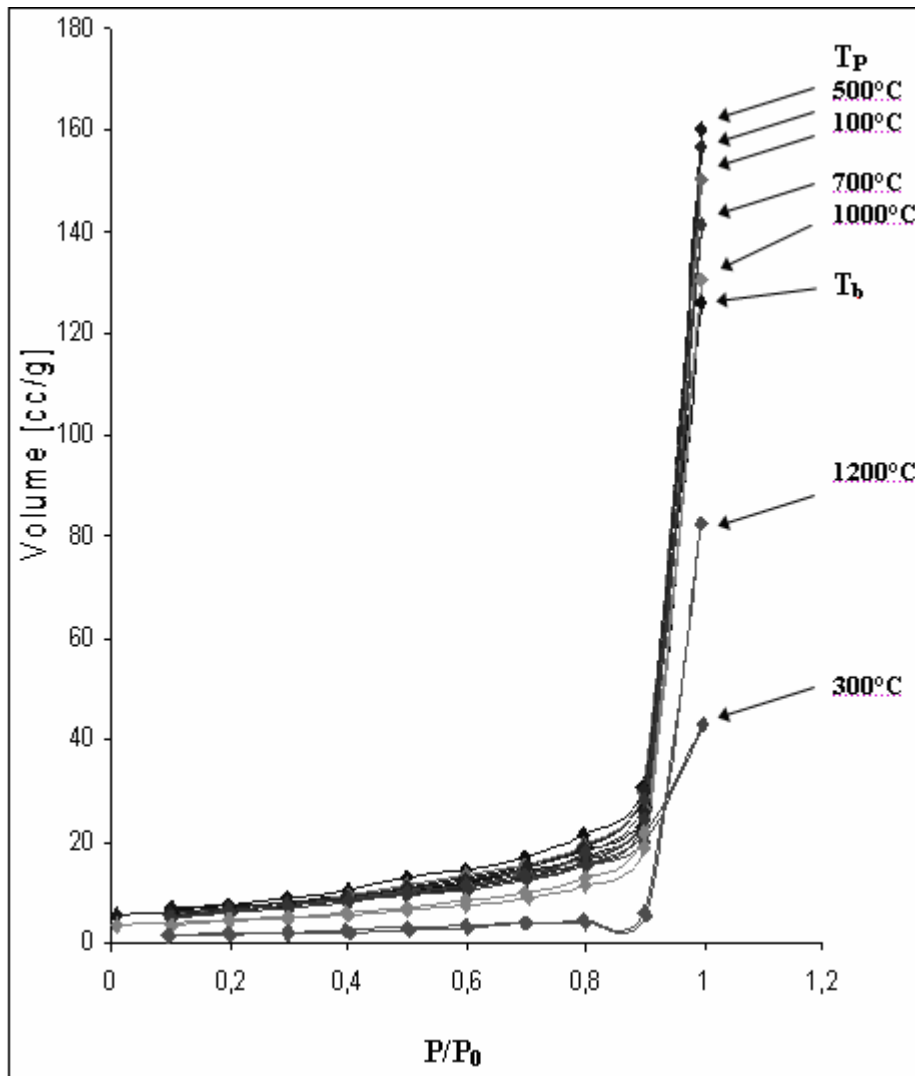


Figure 15: adsorption-desorption isotherms of tabarka samples after thermal treatment

TABLE 7: specific surface of samples after thermal treatment

Temperature (°C)		20	100	300	500	700	1000	1200
Specific surface (m ² /g)	K	233,96	178,80	178,12	149,83	130,01	12,29	0,61
	T	24,57	22,77	23,92	22,15	21,74	15,19	5,92

til 700°C. One will note the extreme stability of the total surface developed by this clay during the phase of the dehydroxylation. Therefore the dehydroxylation doesn't entail any modifications important of the texture of the kaolinite.

The representation of the evolution of the specific surface of Kasserine clay, according to the temperature (Figure 17) show that:

- A slightly decreases of the surface in the begin of the dehydroxylation.
- The surface remains constant in the second stage

of the dehydroxylation (100°C to 700°C). One will note the extreme stability of the total surface developed by kasserine sample during this phase.

- An abrupt diminution at 700°C that is interpreted by a process of sintering.

Full Paper

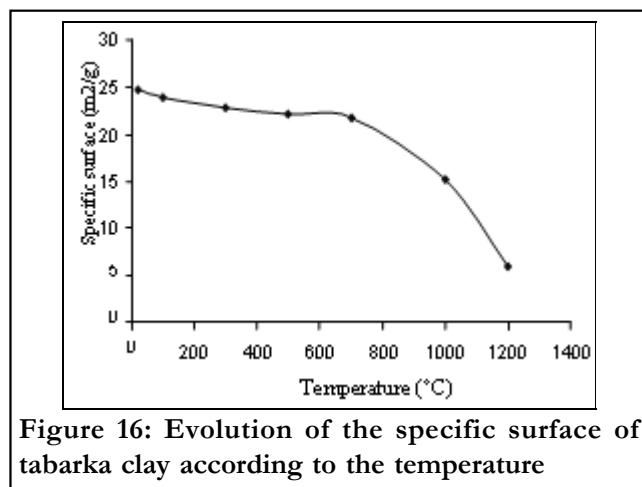


Figure 16: Evolution of the specific surface of tabarka clay according to the temperature

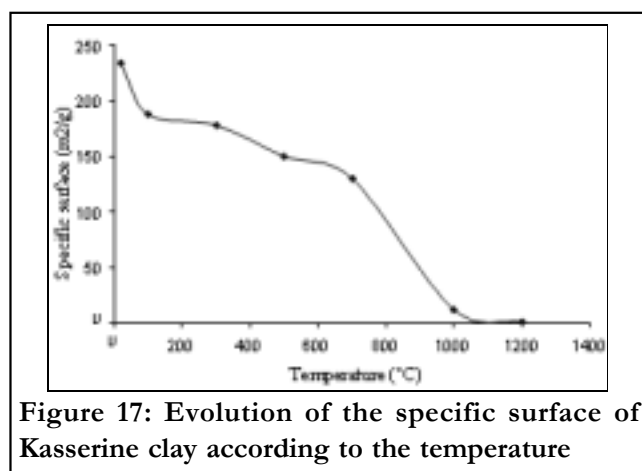


Figure 17: Evolution of the specific surface of Kasserine clay according to the temperature

CONCLUSION

The selected clays differ by their mineralogical properties. The tabarka is a well-crystallized kaolinite. Whereas the Kasserine clay is a hydrated halloysite characterized by a important specific surface (233.96 m²/g). The evolution of specific surface according to the temperature of the Kasserine samples after thermal treatment shows an abrupt diminution at 700°C that are interpreted by a process of sintering. The thermal treatment of the two clays at 1200°C, shows the apparition of a new phase that is the mullite. This mullite is identical to mullite gotten by the process sol-gel from the synthesis of the pure aluminosiloxane.

REFERENCES

[1] M.M.Jordan, A.Boix, T.Sanfelieu, C.De la Fuente; Applied Clay Science, **14**, 225-234 (1999).

- [2] D.S.Perera; DSIR, Private Bag, Petone, New Zealand, (1985).
- [3] Qinfu Liu, D.A.Spears, Qinpu Liu; Applied Clay Science, **19**, 89-94 (2001).
- [4] Van Olphen; 'An Introduction to Clay Colloid Chemistry', Interscience Publisher, (1963).
- [5] Z.Soljic, V.Marjanovic-krajovan; Chimie Analytique, **50**, 3 (1968).
- [6] E.Galan, P.Aparicio, A.Miras, K.Michailidis, A.Tsiram-bides; Applied Clay Science, **10**, 477-490 (1996).
- [7] G.W.Brindley, K.Robinson; Mineral.Mag., 242-253 (1946).
- [8] M.Mehmel; Z.Krist., 35-43 (1935).
- [9] G.Brindley, G.Brown; 'Crystal Structures of Clay Minerals and their X-ray Identification', Mineralogical Society, London, (1984).
- [10] N.J.Saikia, D.J.Bharali, P.Sengupta, D.Bordoloi, R.L.Goswamee, P.C.Saikia, P.C.Borthakur; Applied Clay Science, **24**, 93-103 (2003).
- [11] V.Balek, M.Murat; Thermochim, **282-283**, 385-397 (1996).
- [12] A.K.Chakravorty; Journal of Thermal Analysis, **39**, 289-299 (1993).
- [13] M.Murat; Cem.Concr.Res., **13(2)**, 511-518 (1983).
- [14] C.S.Ross, P.F.Kerr; The kaolins minerals, U.S. Geol.Surv, Profess.Paper, **165(E)**, 151-175 (1931).
- [15] J.J.Fripiat, J.Chaussidon, et Azelli; Chimie Physique des phenomenes de surface, Masson et Cie, (1971).
- [16] W.P.Kelley; 'Cation Exchange in Soils', Reinhold, New York, (1948).
- [17] B.Sonuparlak, M.Sarikaya, A.Aksay; Journal of American Ceramic Society, **11**, 70, 837-842 (1987).
- [18] M.F.De Souza, J.Yamamoto; Ceramica, **45**, 291, Sao Paulo Jan./Feb., (1999).
- [19] G.Kakali, T.Perraki, S.Tsivilis, E.Badogianni; Applied Clay Science, **20**, 73-80 (2001).
- [20] D.R.Treadwell, D.M.Dabbs, I.A.Aksay; Chem. Mater., **8**, 8, 2056-2060 (1996).